



Full length article

## Life cycle assessment of low temperature asphalt mixtures for road pavement surfaces: A comparative analysis

Joao Santos <sup>a</sup>, Sara Bressi <sup>b</sup>, Véronique Cerezo <sup>c</sup>, Davide Lo Presti <sup>d</sup>, Michel Dauvergne <sup>e</sup>

[Show more](#)

<https://doi.org/10.1016/j.resconrec.2018.07.012>

[Get rights and content](#)

### Highlights

- Comparative life cycle assessment of low temperature asphalt mixtures applied in surface layers.
- The foamed-based WMA mixture with 50% RAP is the most environmentally friendly.
- Environmental benefits can be achieved by fuelling asphalt plants with natural gas.
- The inferior long-term performance of alternative asphalt mixtures offsets the environmental benefits.

Original version of the manuscript:

<https://doi.org/10.1016/j.resconrec.2018.07.012>.

Corresponding author.

[j.m.oliveiradossantos@utwente.nl](mailto:j.m.oliveiradossantos@utwente.nl)

personal contact: [davide.lopresti@nottingham.ac.uk](mailto:davide.lopresti@nottingham.ac.uk)

### Citation

Joao Santos, Sara Bressi, Véronique Cerezo, Davide Lo Presti, Michel Dauvergne, Life cycle assessment of low temperature asphalt mixtures for road pavement surfaces: A comparative analysis, Resources, Conservation and Recycling, Volume 138, 2018, Pages 283-297, ISSN 0921-3449, <https://doi.org/10.1016/j.resconrec.2018.07.012>.

1 **LCA of low temperature asphalt mixtures for road pavement surfaces: a**  
2 **comparative analysis**

3 **Joao Santos, PhD (Corresponding Author)**

4 IFSTTAR, AME-EASE, Route de Bouaye, CS4, F-44341 Bouguenais, France.

5 Email: [santosjmo@gmail.com](mailto:santosjmo@gmail.com)

6 **Sara Bressi, PhD**

7 Department of Civil and Industrial Engineering (DICI), University of Pisa, Largo L. Lazzarino, Pisa,  
8 Italy

9 **Véronique Cerezo, PhD**

10 IFSTTAR, AME-EASE, Route de Bouaye, CS4, F-44341 Bouguenais, France.

11 **Michel Dauvergne**

12 IFSTTAR, AME-EASE, Route de Bouaye, CS4, F-44341 Bouguenais, France.

13 **Davide Lo Presti, PhD**

14 Nottingham Transportation Engineering Centre, University of Nottingham Faculty of Engineering, The  
15 University of Nottingham, University Park, Nottingham, NG7 2RD.

16

17

# LCA of low temperature asphalt mixtures for road pavement surfaces: a comparative analysis

## Abstract

The increasing fuel consumption demand, the accelerated pressure imposed by the depletion of scarce raw materials and the urgent environmental protection requirements are forcing the change of pavement industry and academia community's research endeavors towards the development of low emissions road paving technologies able to significantly reduce mixing and compaction temperature as well as the consumption of virgin raw materials. One set of relatively recent technologies in the field of pavement materials that aims at addressing those concerns are the warm mix asphalt (WMA). In fact, they have the potential to allow the reduction of energy consumption and airborne emissions during their production and placement. Moreover, the incorporation of reclaimed asphalt pavement (RAP) in these mixtures may further improve their potential environmental sustainability, both by reducing the consumption of virgin raw materials, and by reducing the stockpiles and landfills of milled materials. Which of these sustainable practices is greener and whether combining them is promising as it sounds, it's still not actually too well demonstrated in literature.

It's within this context that this study presents a full process-based comparative life cycle assessment (LCA) looking at understanding the environmental impact of reducing mixing temperature, through the use of warm mix technologies, namely chemical additives-based and foamed-based, and different rate of recycling (0% and 50% RAP). Furthermore, the investigation explores the effect of combining the effects in the construction, maintenance and rehabilitation (M&R) of wearing courses for flexible road pavements. The analysis assessed the functional units over a 30-year project analysis period (PAP), considering all pavement life cycle phases: extraction of raw materials and production; transportation of materials; construction, maintenance and rehabilitation; work zone traffic management; usage and end-of-life. The results of this study showed that, for the conditions considered and assumptions performed, a pavement construction and M&R scenario in which a foamed-based WMA mixture with a RAP content of 50% is employed in the wearing course throughout the pavement life cycle is the most environmentally friendly alternative among all the competing solutions. Moreover, the results of a scenario analysis showed that the life cycle environmental impacts could be reduced if the asphalt plant was fueled by natural gas, or if the pavement structure was dismantled at the end of its lifetime and the debris recycled.

**Keywords:** life cycle assessment (LCA); war mix asphalt (WMA); chemical additives; hot mix asphalt (HMA); reclaimed asphalt pavement (RAP); sustainable pavement construction and management.

## 1. Introduction

Considerable amount of Greenhouse gases (GHG) and airborne pollutants are released into the atmosphere during the energy intensive asphalt mixtures production process (Thives and Ghisi, 2017). As GHG and their effect on the climate are increasingly in the spotlight with respect to policy, legislation and general public's concern, the pavement industry and scientific community have been challenged to improve conventional asphalt mixtures production processes by developing more sustainable technologies and behaviors.

One example of the specific engagement of research institutions and enterprises in developing and delivering multi-faceted and sound solutions meant to mitigate the environmental pressure originated by the sector's activities is the SUP&R ITN (Sustainable Pavement & Rail Initial Training Network) research project (<http://superitn.eu/wp/>) (Lo Presti et al., 2017).

The SUP&R ITN is a training-through-research program, which through a multidisciplinary and multi-sectorial network, aims (1) to form a new generation of engineers versed in sustainable technologies for road pavement and railways and (2) to provide, to both academia and industry, design procedures and sustainability assessment methodologies to certify the sustainability of the studied technologies to the benefit of the European community. Some of the promising sustainable technologies commonly mentioned in the literature and studied in the framework of this research project are the asphalt mixes requiring lower manufacturing temperatures, such as (1) warm mix asphalt (WMA) (Kristjánssdóttir et al., 2007; Hamzah et al., 2010; Tatari et al., 2012; Vidal et al., 2013; Mohammad et al., 2015; Rodríguez-Alloza et al., 2015; Almeida-Costa and Benta, 2016; Stimilli et al., 2017), (2) half-warm mix asphalt (HWMA) (Rubio et al., 2013) and (3) cold mix asphalt technologies (FHWA, 2016).

WMA is the name used to designate a set of technologies by which the traditional HMA is allowed to be manufactured, transported, placed and compacted at lower temperatures. Characteristically, the mixing temperatures of HMA vary from 150 to 180°C (Jones, 2004), whereas for WMA and HWMA they are comprised between 100 and 140°C, and between 60 and 100°C, respectively. In addition to the mixing temperature reduction, the list of benefits that come with the use of these technologies is completed with the following items (Rubio et al., 2013): (1) reduced emissions; (2) better working conditions due to the absence of harmful gases; (3) quicker turnover to traffic; (4) longer hauling distances; and (5) extended paving window. Furthermore, the potential sustainability of such solutions may be further broadened through the partial or full replacement of virgin and/or manufactured materials with recycled, co-product, or waste materials (RCWM), from which the reclaimed asphalt pavement (RAP), recycled concrete aggregate (RCA), recycled asphalt shingles (RAS), air-cooled blast furnace slag (ACBFS), steel furnace slag (SFS), foundry sand, etc., (Van Dam et al., 2016) are examples.

In order to prove quantitatively the theoretical environmental benefits to which the aforementioned technologies are associated with, the most significant environmental inputs and outputs over their life cycle, from raw materials production to the end of the technologies' life, should be assessed. This can be accomplished through life cycle assessment (LCA). LCA is a data-driven, systematic methodology, to investigate, estimate, and evaluate the environmental burdens caused by a material, product, process, or service throughout its life span (Matthews et al., 2015). The life cycle begins at the acquisition of raw materials, evolves through several distinct stages (material processing, manufacturing and use), and terminates at the product end-of-life (EOL).

### 1.1. State-of-the-art of LCA studies on WMA technologies

Several research studies have been performed that apply the LCA methodology to measure the potential life cycle environmental impacts of the processes involving the production and placement of the WMA technologies in lieu of conventional HMA. Tatari et al. (2012) developed a thermodynamic-based hybrid LCA model to evaluate the environmental impacts from an ecological resource accounting

1 perspective of three types of WMA mixtures and compare them to those of a conventional HMA  
2 mixture. The following WMA technologies were assessed: Aspha-Min<sup>®</sup>, Sasobit<sup>®</sup>, and Evotherm<sup>®</sup>  
3 WMA. Vidal et al. (2013) performed a comprehensive LCA of road pavements including HMA and  
4 zeolite-based WMA, both with and without RAP content. The ReCiPe method was used to assess the  
5 environmental impacts according to two sets of impact categories: midpoint and endpoint categories.  
6 Additionally, the cumulative energy demand indicator was adopted to compare the mixtures in terms of  
7 energy consumption. Mohammad et al. (2014) compared the environmental performance of two WMA  
8 technologies, namely foaming and Sasobit<sup>®</sup> additive, to that of a conventional HMA mixture, in terms  
9 of energy consumption at the asphalt plant and CO and CO<sub>2</sub> emissions monitored during their  
10 production and placement. Rodríguez-Alloza et al. (2015) performed a comprehensive hybrid input-  
11 output-based LCA of the production of Fischer Tropsch (F-T) wax-based WMA mixtures with and  
12 without crumb-rubber modified (CRM) binders. The potential benefits of that WMA technology in  
13 relation to a conventional HMA were quantified by accounting for the embodied energy requirement  
14 and GHG emissions in the supply chain. Giani et al. (2015) carried out a process-based LCA in  
15 collaboration with an Italian asphalt-producing company with the objective of quantifying the potential  
16 environmental benefits resulting from constructing asphalt pavement using an unspecified type of  
17 WMA with the incorporation of up to 30% of RAP. Almeida-Costa and Benta (2016) quantified the  
18 potential benefits of two WMA technologies, Rediset<sup>®</sup> and Sasobit<sup>®</sup> additives, in relation to a  
19 conventional HMA mixture, by assessing the energy consumption and GHG emissions associated with  
20 their production. In turn, Yang et al. (2017) compared the environmental performance of crumb-rubber  
21 modified HMA and Evotherm<sup>®</sup> WMA to that of a conventional HMA mixture, expressed in terms of  
22 energy consumption and hazard emissions associated with their production.

## 23 24 **1.2. Aim and purpose of the study**

25 Notwithstanding the merits of the studies listed previously in showing the potential environmental  
26 benefits of some WMA technologies, mostly in terms of energy consumption and emissions released  
27 during their production, several aspects can be pointed out which underpin the need of expanding the  
28 knowledge in this domain: (1) there is still a wide range of other WMA technologies equally worthy of  
29 being thoroughly analyzed; (2) the role of the upstream supply chain related to the production of  
30 chemical additives used in WMA mixtures is commonly excluded from the system boundaries; (3) the  
31 existing studies tend to narrow the system boundaries by focusing on a few life cycle phases, usually  
32 the materials extraction, mixtures production and construction phases, and thus excluding phases (i.e.,  
33 work zone (WZ) traffic management, usage and EOL), which depending on the technical context, might  
34 drive the environmental performance of the system being analysed. Moreover, while the consideration  
35 of the last point is not methodologically wrong, provided that a given set of conditions are met, it  
36 constrains a more global view of the system and thereby opportunities for eventually more meaningful  
37 environmental improvements.

38 Given the issues abovementioned, this research study aims to perform a comprehensive and  
39 methodologically sounded pavement LCA of a road pavement section incorporating several WMA  
40 technologies (i.e., chemical additives and foamed-based), both with and without RAP content, which  
41 covers all the pavement life cycle phases, from raw material acquisition, via production and use phases,  
42 to the EOL phase.

43 The overall purpose is to increase the pavement community stakeholders' capacity to make more  
44 strategic and informed decisions regarding the construction and M&R of road pavement that would  
45 ultimately enhance the sustainability of pavement systems.

## 2. Methodology

A comparative process-based LCA study is performed taking into account the ISO 14040 series (ISO, 2006a; ISO, 2006b) and the Federal Highway Administration's (FHWA's) Pavement LCA Framework (Harvey et al., 2016). It calculates and compares the potential environmental impacts of different asphalt mixtures adopted in the construction and M&R of a road pavement section during its life cycle.

The stages adopted in this study include goal and scope definition, inventory analysis, impact assessment, and interpretation.

### 2.1. Goal and scope definition

#### 2.1.1. Goal

The main goal of this paper is to quantify the potential life cycle environmental impacts of a flexible road pavement section throughout its life cycle. The road pavement section studied involves the use of conventional and low-temperature asphalt mixes, with and without RAP content, in the construction, maintenance and rehabilitation (M&R) of wearing courses of the flexible road pavements.


The comparative findings of this study are intended to be used by highway agencies and pavement practitioners to make more assertive judgments on the pros and cons associated with the use of emerging and commonly called sustainable strategies and practices for road pavement construction and M&R.

#### 2.1.2. System description and boundaries

The system boundaries define the unit processes considered in the LCA study and were drawn to cover the pavement life cycle from a cradle-to-grave perspective, and to enable the performance of a parallel life cycle costs analysis in the near future.

Figure 1 presents the pavement life cycle phases and processes included within the system boundaries of the proposed pavement LCA model as well as their positioning towards relevant literature for the subject. Specifically, the system boundaries entail six pavement life cycle phases, modeled through individual but interconnected modules. They are the following: (1) extraction of materials and mixtures production, consisting of the acquisition and processing of raw materials, and the mixing process of asphalt mixtures in plant; (2) construction and M&R, including all construction and M&R procedures and related construction equipment usage; (3) transportation of materials, accounting for the transportation of materials to and from the construction site and between intermediate facilities (e.g., transportation of aggregates from the quarries to asphalt mixing plants, etc.); (4) WZ traffic management phase. The WZ traffic management costs consist of the additional costs borne by the road users (RUC) when facing a disruption of the normal traffic flow as a consequence of the constraints imposed by a WZ traffic management plan; (5) usage, which addresses the interactions of the pavement with vehicles and environment throughout the project analysis period (PAP); and (6) EOL, which models the destination of the pavement structure after the PAP.

The analysis boundaries for the road pavement were set at the sub-base and at the finished road surface. They include (1) the construction of all layers contained by the limits stated above and subsequent M&R activities; (2) the extraction of the materials needed to produce the mixtures used in those layers; and (3) the movement involved in hauling materials between facilities, between facilities and work site, and vice-versa. Furthermore, given the comparative nature of the study, it might have been decided to constraint the LCA system boundaries to the construction and M&R of the wearing course. However, the whole pavement structure was taken into account in order to enable the acquirement of knowledge on the relative contribution of each pavement life cycle phases to the total life cycle impact scores.

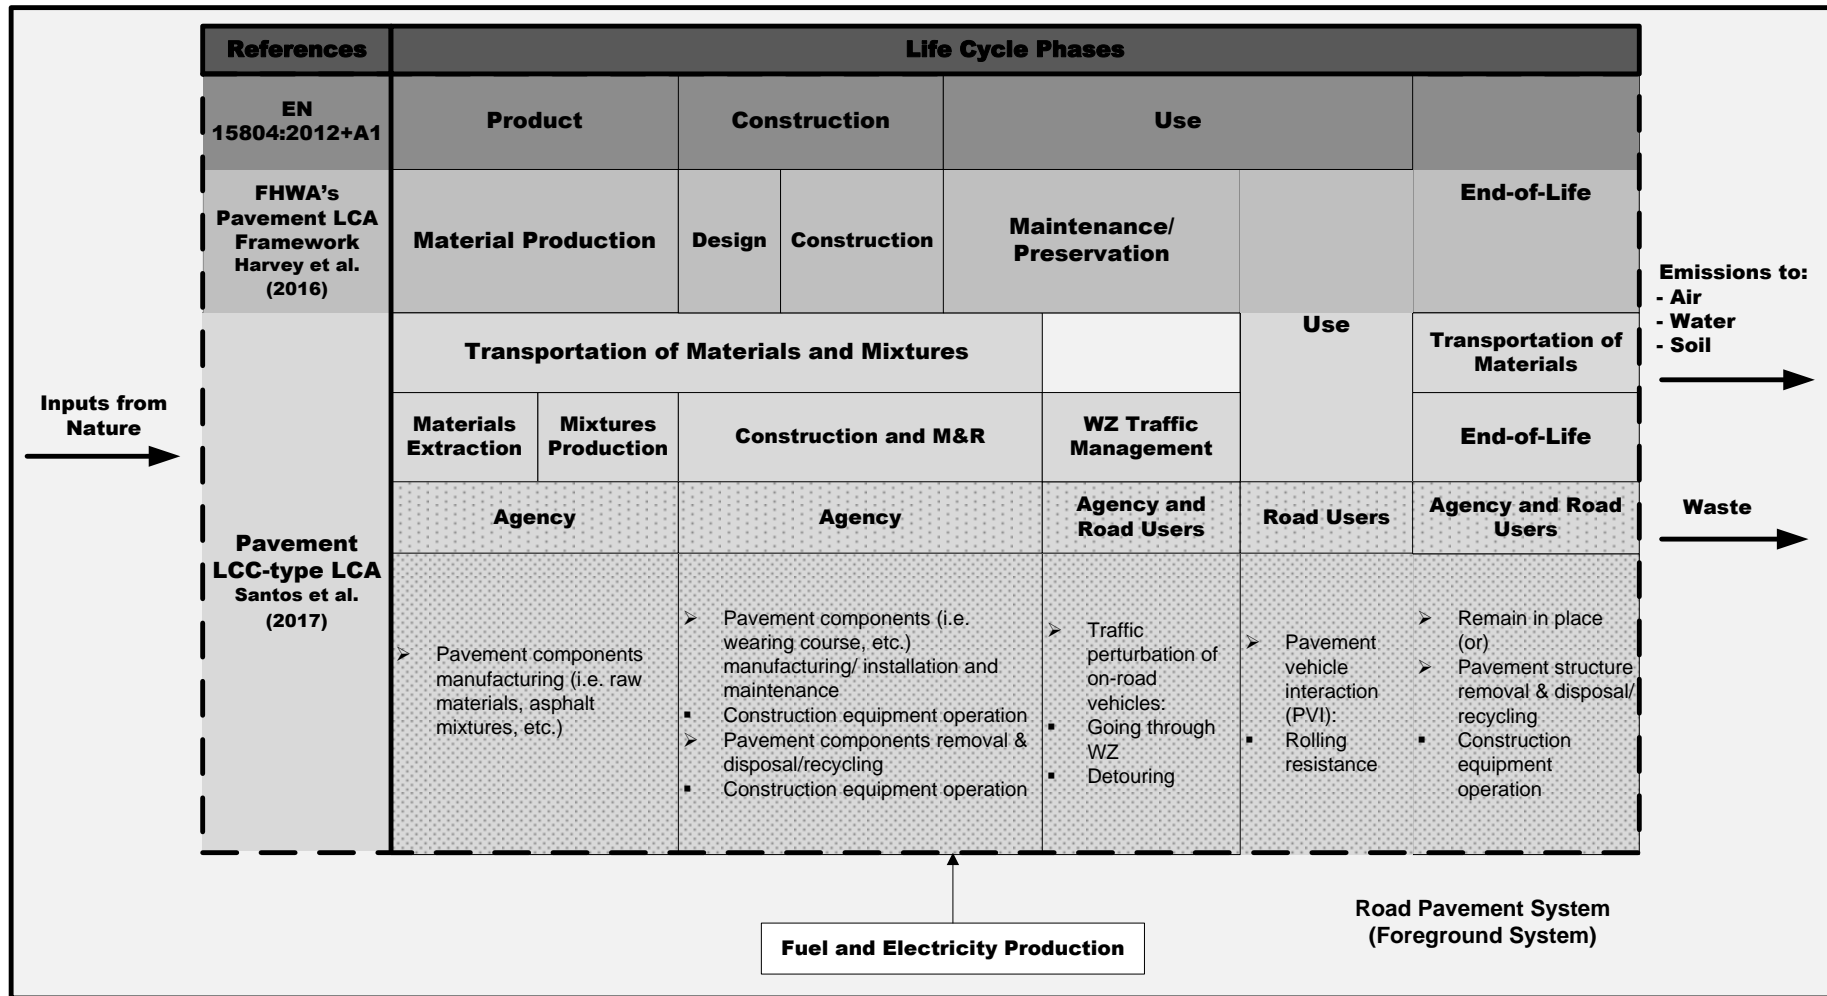

Background System

1  
2 Figure 1. Pavement life cycle phases and processes included in the system boundaries and their positioning towards relevant literature for the subject. (Acronyms:  
3 LCA- life cycle assessment; LCC- life cycle costs; M&R- maintenance and rehabilitation; WZ- work zone)

1 As far as the system boundaries for RAP are concerned, it is assumed that prior to its utilization  
2 the material is processed via a crushing operation, which reduces the variable RAP fragments to uniform  
3 size in order to promote final blend consistency. The environmental burdens resulting from milling or  
4 removing the pavement and hauling the debris from the work site to the recycling unit were not included  
5 into the system boundaries on the basis of a “cut-off” approach (Schrijvers et al., 2016a), which is the  
6 most-widely used procedure to handle the EOL phase in pavements LCAs (Aurangzeb et al., 2014).  
7 According to this approach, if a product is recycled at the EOL phase, no impacts for waste management  
8 are considered. The impacts of the recycling process are attributed to the second life cycle (Schrijvers  
9 et al., 2016b). Thus, the post-processing of the debris materials towards their transformation into usable  
10 RAP is only accounted for when considering the production of new mixtures which incorporate RAP  
11 into their composition. To accomplish the RAP processing task, a crusher unit located within the asphalt  
12 plant facility is considered, which consists of (1) a diesel-powered crusher, (2) a diesel-powered mobile  
13 screening plant, (3) an electrically-powered stackable conveyor and (4) a wheel loader.

14 The upstream emissions and resources consumption associated with the production of the energy  
15 sources used to power the different processes, construction equipment, and on-road vehicles were also  
16 included in the system boundaries. On the other hand, construction equipment, road-related safety and  
17 signaling equipment (including road marking), road accessories (fences, road lighting software, etc.),  
18 and the earthworks required to build the platform over which the pavement foundation will be built  
19 were not included in the system boundaries. The earthworks were excluded because the potential  
20 environmental impacts related to those works are better handled when performing a road LCA, as they  
21 are specific to a particular project. This fact makes it unsuitable for the general application of a  
22 pavement LCA model as it is intended in this case study.

23 Various supplementary sub-models that are attached to the corresponding modules, as well as the  
24 data required to run those models, are introduced and discussed later in this paper.

### 25 2.1.3. *Functional unit*

26 The functional unit is the central core of any LCA and forms the basis for comparisons between  
27 different systems with the same utility for the same function. In the pavement domain, this means a unit  
28 of pavement that can safely and efficiently carry the same traffic over the same project analysis period  
29 (PAP). Then, it is defined by their geometry, service life, and levels of traffic supported.


#### 30 2.1.3.1. *Case study features: traffic, service life, pavement structure and maintenance and* 31 *rehabilitation strategy*

32 The functional unit of the case study presented in this paper is a typical French highway section of  
33 1-km length, composed of two independent roadways, each with 2 lanes with an individual width of  
34 3.5m. The PAP is 30 years, starting in 2015. The initial two-way average annual daily traffic (AADT)  
35 was considered to be equal to 6500 vehicles/day, of which 33% are heavy duty vehicles (HDV) equally  
36 divided between rigid HDV and articulated HDV. The structure and composition of the French fleet of  
37 vehicles, expressed in terms of type of vehicles and European emissions standards, was that defined by  
38 CITEPA (*Centre Interprofessionnel Technique d'Études de la Pollution Atmosphérique*). The traffic  
39 growth rate was set equal to 1.5% per year (Jullien et al., 2015). The geometric characteristics of the  
40 pavement structure adopted in each of the independent roadways are presented in Figure 2. A flexible  
41 road pavement structure was selected because this type of pavement represents the overwhelming  
42 majority of the total extension of the French highway network.

43 As for pavement maintenance, a pavement M&R strategy derived from French practice was  
44 considered (Jullien et al., 2014; Jullien et al., 2015). Figure 2 displays the maintenance tasks inherent  
45 to each M&R activity as well as the application timing. They were assumed to be the same irrespective  
46 of the type of mixture applied in the wearing course. This assumption is supported by research studies



1 showing that HMA and WMA pavements have comparable long-term field performance in terms of  
 2 structural durability (Washington State University et al., 2017) and the inexistence of solid scientific  
 3 evidences that functional properties of HMA and WMA pavements will evolve distinctively over time.  
 4

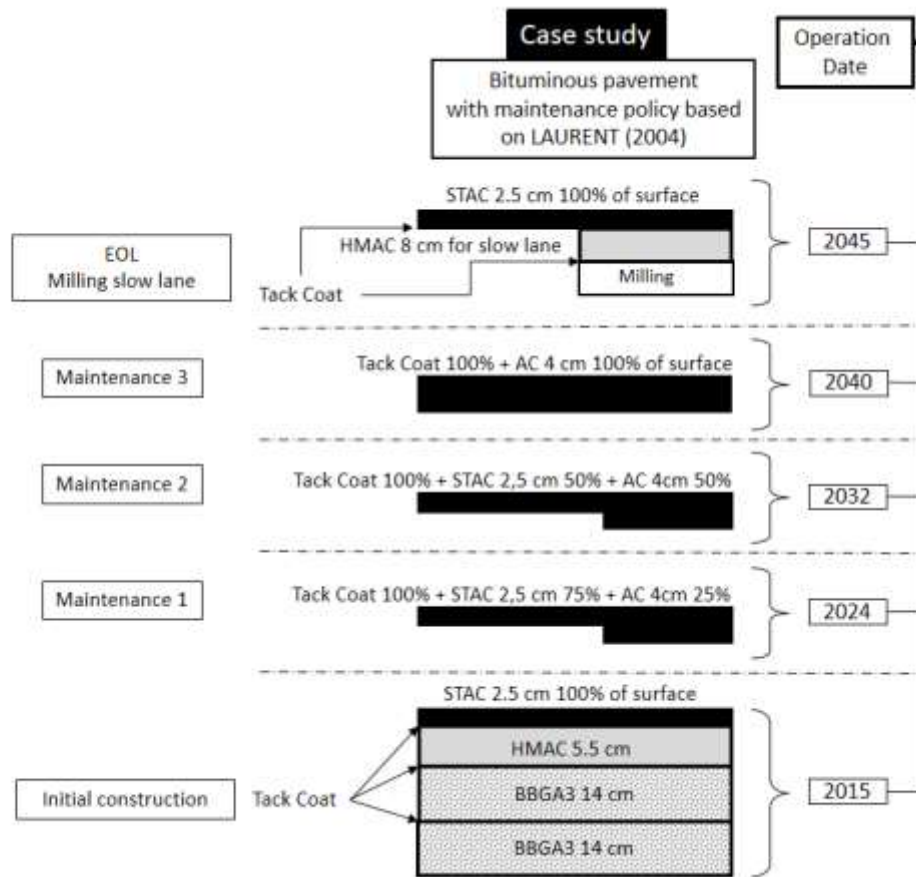

5  
 6 **Figure 2. Geometric characteristics of the flexible pavement structure and M&R strategy. (Acronyms:**  
 7 **BBGA- bituminous bound graded aggregate; HMAC- hot mix asphalt concrete; STAC- super thin asphalt**  
 8 **concrete; AC- asphalt concrete)**

9 **2.1.3.2. Case study features: mixtures composition**

10 In order to understand the potential environmental advantages and disadvantages related to the use,  
 11 in wearing courses, of low-temperature asphalt mixes with and without RAP content, the reference  
 12 pavement structure (Figure 2) constituted by layers made of conventional HMA without RAP content  
 13 was compared to four alternative structures with equal geometry, but in which the wearing course of  
 14 the initial structure, and subsequent M&R treatments, was made of WMA produced according with two  
 15 different technologies (i.e., foaming and CECABASE® additive) to lower the manufacturing  
 16 temperature, and with and without the adding of RAP. Furthermore, the set of alternative mixtures was  
 17 completed with the consideration of a conventional HMA with a RAP content equal to 50%, thus rising  
 18 to 6 the total number of pavement sections to be analysed and compared. Table 1 presents the features  
 19 of the several mixtures analyzed in the case study, which were investigated in the scope of the SUP&R  
 20 ITN research project (Lo Presti et al., 2017).  
 21

22 **Table 1. Features of the bituminous mixtures used in all pavement structures studied.**

| Item | Type of mixture |
|------|-----------------|
|------|-----------------|

|                                               | HMA, 0%<br>RAP | WMA-<br>CECABASE®,<br>0% RAP | Foamed<br>WMA, 0%<br>RAP | HMA,<br>50%<br>RAP | WMA-<br>CECABASE®,<br>50% RAP | Foamed<br>WMA,<br>50% RAP |
|-----------------------------------------------|----------------|------------------------------|--------------------------|--------------------|-------------------------------|---------------------------|
| <i>Virgin aggregate</i>                       |                |                              |                          |                    |                               |                           |
| Quantity (%/m)                                | 94.4           | 94.4                         | 94.4                     | 48.4               | 48.37                         | 48.36                     |
| Water content<br>(%/a)                        | 3              | 3                            | 3                        | 3                  | 3                             | 3                         |
| <i>RAP</i>                                    |                |                              |                          |                    |                               |                           |
| Quantity (%/m)                                | -              | -                            | -                        | 48.4               | 48.37                         | 48.36                     |
| Water content<br>(%/RAP)                      | -              | -                            | -                        | 3                  | 3                             | 3                         |
| <i>Bitumen</i>                                |                |                              |                          |                    |                               |                           |
| Penetration grade                             | 35/50          | 35/50                        | 35/50                    | 35/50              | 35/50                         | 35/50                     |
| Quantity (%/m)                                | 5.4            | 5.4                          | 5.4                      | 3.2                | 3.2                           | 3.2                       |
| <i>WMA agent</i>                              |                |                              |                          |                    |                               |                           |
| Type                                          | -              | surfactant                   | water                    | -                  | Surfactant                    | water                     |
| Quantity (%/m)                                | -              | 0.054                        | 0.077                    | -                  | 0.054                         | 0.077                     |
| <i>Mixture density<br/>(kg/m<sup>3</sup>)</i> |                |                              |                          |                    |                               |                           |
|                                               | 2360           | 2340                         | 2260                     | 2370               | 2360                          | 2360                      |

1 Acronyms: HMA- hot mix asphalt; WMA- warm mix asphalt; RAP- reclaimed asphalt pavement; %/m-  
2 percentage by mass of mixture; %/a- percentage by mass of aggregates; %/RAP- percentage by mass of RAP.

### 3 2.1.4. Data sources and data quality requirements

4 The inventory data required to perform a LCA study are classified into two categories: primary  
5 and secondary data. Primary data are those specific to the production processes for the product or service  
6 studied in the LCA. In turn, secondary data represent generic or average data for the product or service  
7 subject to analysis. (EC, JRC - IES, 2010).

8 In this study the data sources were selected in order to be as much time, geographical and  
9 technological representative as possible. That means that the most recent and truthful data representing  
10 French processes and conditions were used as inputs and outputs when modelling the processes covered  
11 by the several sub-components integrating the system boundaries. Specifically, the primary data include  
12 mainly: (1) the composition of the mixtures; (2) the annual fuel consumption (FC), production and life  
13 period of asphalt mix plants; (3) transportation distances; (3) construction vehicles fleet composition;  
14 and (4) on-road vehicles fleet composition;

15 Regarding the secondary data, they are mainly related to the inventory analysis of (1) raw  
16 materials, (2) fuels, and (3) construction, transportation, and on-road vehicles operation, and they were  
17 obtained from existing publicly available reports and the ecoinvent database version 3.2, but modified  
18 whenever possible and suitable to best approximate French conditions by using French energy  
19 inputs/mixes.

## 20 2.2. Life cycle inventory

21 The life cycle inventory (LCI) stage consists of the real data collection and modelling of the system.  
22 In addition to the data sources, it relies on the several models selected for modelling the processes  
23 analyzed by the several considered sub-systems that make up the whole system.

### 24 2.2.1. Materials extraction and mixtures production phase

25 This pavement LCA phase addresses the environmental burdens arising from the acquisition and  
26 processing of the materials applied during the initial construction and future M&R of a road pavement  
27 segment. This includes all materials manufacturing processes, from extraction of raw materials to their  
28 transformation into a pavement input material (material extraction sub-phase), ending with the mixture

1 production at a mixing plant (materials production sub-phase). The latter sub-phase accounts for the  
2 environmental burdens associated with the operation of the (1) mixing plant (i.e., dryer, hot screen,  
3 mixers, etc.), (2) wheel loader during the movement of aggregates from the stockpiles to the feed bins  
4 (3) electronic group of the asphalt plant setup and (4) RAP processing unit so that the RAP ensures the  
5 required properties to be incorporated into a new asphalt mixture.

#### 6 2.2.1.1. *Materials extraction sub-phase*

7 The virgin aggregates required to produce the asphalt mixtures were modelled as gravel and the  
8 LCI data associated with their production were obtained from the unit process “*gravel, crushed / gravel*  
9 *production, crushed*” of the ecoinvent database. Also taken from the aforementioned database was the  
10 LCI data corresponding to the asphalt binder production “*pitch / petroleum refinery operation*”.  
11 Regarding the bituminous emulsion production, the formulation and the consumption of energy  
12 resources defined in Eurobitumen report (Eurobitumen, 2011) were considered and combined with the  
13 LCI data associated with the production and transport of the corresponding items existing in the  
14 ecoinvent database version 3.2.

15 In one of the WMA production technologies considered in this study, CECABASE® was used as a  
16 chemical additive. According to the scarce information available, this additive is made up of fatty acids,  
17 namely tetraethylenepentamine polyamides  
18 ([http://www.cladding.com.au/Images/common/stakeholder-relations/asphalt-vic/Deer-Park-MSDS-](http://www.cladding.com.au/Images/common/stakeholder-relations/asphalt-vic/Deer-Park-MSDS-Ceca-RT945.pdf)  
19 [Ceca-RT945.pdf](http://www.cladding.com.au/Images/common/stakeholder-relations/asphalt-vic/Deer-Park-MSDS-Ceca-RT945.pdf)). Due to the inexistence in the literature of LCI data referring to its production, the  
20 ecoinvent database process “*market for fatty acid / fatty acid / cut-off, U*” was used as proxy.

21 As for the RAP processing, the common production rates of the several machines integrating the  
22 processing unit were considered when determining the energy requirements. The LCI data related to  
23 the production and distribution of those energy resources representing the French conditions were  
24 posteriorly taken from the ecoinvent database.

#### 25 2.2.1.2. *Mixtures production sub-phase*

26 This sub-phase addresses the LCI of the asphalt production process by considering different types  
27 of mixes, both with and without the incorporation of RAP in their formulations. In this case study it  
28 was assumed that all asphalt mixes were produced through a conventional heavy fuel oil (HFO)-fired  
29 batch mix plant. The asphalt plant operation takes into account the infrastructure and machinery used  
30 in mixes production. The period of life of the plant was estimated to be about 25 years. This value was  
31 obtained by considering the average yearly production (80,000 tons) and the average life time  
32 production (2,000,000 tons) of a typical French asphalt plant. The energy required for storing the binder  
33 in the asphalt plant, the fuel consumed by the wheel loader and the electricity consumed by the electric  
34 group of the asphalt plant were respectively 40 MJ, 0.194 liters and 5 MJ per ton of asphalt mix  
35 produced and correspond to the average French practices.

36 In order to capture the consequences in the energy requirements due to the variations in  
37 composition and manufacturing temperature of the several types of mixtures as well as the moisture  
38 content and initial temperature of the raw materials, the thermal energy (TE) required to produce the  
39 asphalt mixtures was determined through an energy balance represented by Equation (1). The values of  
40 the parameters in that equation are presented in Table 2 and were based on the literature and conditions  
41 commonly found in the real practice.

$$TE = \left[ \sum_{i=0}^M m_i \times C_i \times (t_{mix} - t_0) + m_{bit} \times C_{bit} \times (t_{mix} - t_0) + \sum_{i=0}^M m_i \times W_i \times C_w \times (100 - t_0) \right. \\ \left. + L_v \times \sum_{i=0}^M m_i \times W_i + \sum_{i=0}^M m_i \times W_i \times C_{vap} \times (t_{mix} - 100) \right] \times (1 + CL) \quad (1)$$

Where  $TE$  is the thermal energy (MJ/tonne mixture) required to produce the asphalt mixtures,  $m_i$  is mass of aggregates of fraction  $i$ ,  $M$  is the total number of aggregates fractions,  $C_i$  is the specific heat capacity coefficient of aggregates of fraction  $i$ ,  $t_{mix}$  is the mixing temperature of an asphalt mixture,  $t_0$  is the ambient temperature,  $m_{bit}$  is the mass of bitumen,  $C_{bit}$  is the specific heat capacity coefficient of bitumen,  $W_i$  is the water content of aggregates of fraction  $i$ ,  $C_w$  is the specific heat capacity coefficient of water,  $L_v$  is the latent heat required to evaporate water,  $C_{vap}$  is the specific heat capacity coefficient of water vapor,  $CL$  is the casing losses factor. Casing losses are thermal energy used to heat plant iron (for example, the shell of the drum) and then radiated to the atmosphere, rather than being used to heat the mixture components (West et al., 2014). This factor was considered to be same for all mixtures studied and was calculated as the difference between the average value of the energy required to produce a conventional HMA in France and that calculated according to the energy balance described above. That means that the unexplained differences in the calculated energy are attributed to casing losses.

**Table 2. Values of the parameters considered in Equation (1).**

| Name                                                                                            | Value  | Unit                    |
|-------------------------------------------------------------------------------------------------|--------|-------------------------|
| $t_0$ -Ambient temperature                                                                      | 15     | °C                      |
| $t_{HMA,0\% RAP}$ -Mixing temperature of HMA, 0% RAP mixture                                    | 160    | °C                      |
| $t_{HMA,50\% RAP}$ -Mixing temperature of HMA, 50% RAP mixture                                  | 160    | °C                      |
| $t_{WMA-CECABASE,0\% RAP}$ -Mixing temperature of WMA- CECABASE <sup>®</sup> , 0% RAP mixture   | 130    | °C                      |
| $t_{WMA-CECABASE,50\% RAP}$ -Mixing temperature of WMA- CECABASE <sup>®</sup> , 50% RAP mixture | 130    | °C                      |
| $t_{foamedWMA,0\% RAP}$ -Mixing temperature of Foamed WMA, 0% RAP mixture                       | 130    | °C                      |
| $t_{foamedWMA,50\% RAP}$ -Mixing temperature of Foamed WMA, 50% RAP mixture                     | 130    | °C                      |
| $C_{agg}$ - Specific heat of virgin aggregates <sup>a</sup>                                     | 0.74   | KJ/Kg°C                 |
| $W_{agg}$ - Water content of aggregates                                                         | 3      | % by mass of aggregates |
| $C_{RAP1}$ - specific heat of RAP <sup>a</sup>                                                  | 0.74   | KJ/Kg°C                 |
| $C_{water}$ - specific heat of water at 15 °C                                                   | 4.1855 | KJ/Kg°C                 |
| $L_v$ - latent heat of vaporization of water                                                    | 2256   | kJ/kg                   |
| $C_{vap}$ - specific heat of water vapor                                                        | 1.83   | kJ/kg                   |
| $C_{bit}$ - Specific heat of bitumen                                                            | 2.093  | KJ/Kg°C                 |
| $CL$ - casing loses factor <sup>b</sup>                                                         | 27     | %                       |

Notes: <sup>a</sup>value for granitic aggregates; <sup>b</sup>this value is consistent with the finding of research studies existing in the literature (West et al., 2014).

In order to determine the process air emissions resulting from the mixes production, a methodology based on that developed by Santos et al. (2017) was applied. Firstly, the LCI data corresponding to the process “heat production, heavy fuel oil, at industrial furnace 1MW | heat, district or industrial, other than natural gas | cut-off, U” existing in the ecoinvent database was taken as reference when modeling the operation of the burner existing in the asphalt plant during the production of a conventional HMA

with 0% RAP. Secondly, for the remaining mixes an emission factor (EF) multiplier was determined through the ratio between the thermal energy computed with Equation (1) for those mixes and that for the reference mix. Finally, the output flows expressed in terms of the GHG and the most common airborne substances released during mixes production were derived by multiplying the outputs flows taken as reference by the EF multipliers. The values of the EF multipliers as well as the thermal energy required to produce 1 ton of the mixtures studied are shown in Table 3. The fuel savings presented in this table are consistent with those commonly reported in the literature for both European (D'Angelo et al., 2008) and US (Mohammad et al., 2014) practices, according to which the reduction of the fuel consumption might amount to 11-35% and 12-14%, respectively, the latter expressed in terms of fuel costs. These ranges of values support the validity of the thermal energy model developed.

**Table 3. Thermal energy (TE) required to produce 1 tonne of the mixtures studied and respective emission factor (EF) multipliers.**

|                           | Type of mixture |                       |                    |              |                        |                     |
|---------------------------|-----------------|-----------------------|--------------------|--------------|------------------------|---------------------|
|                           | HMA, 0% RAP     | WMA-CECABASE®, 0% RAP | Foamed WMA, 0% RAP | HMA, 50% RAP | WMA-CECABASE®, 50% RAP | Foamed WMA, 50% RAP |
| TE (MJ/tonne mixture)     | 255             | 226                   | 226                | 251          | 222                    | 222                 |
| TE (Kg HFO/tonne mixture) | 6.05            | 5.35                  | 5.35               | 5.96         | 5.26                   | 5.26                |
| EF (%)                    | -               | 89                    | 89                 | 99           | 87                     | 87                  |

Acronyms: TE- thermal energy; HFO- heavy fuel oil. Notes: Lower Heating Value of HFO was considered to be equal to 42.18 MJ/Kg (IEA, 2005).

### 2.2.2. Construction and M&R phase

In the construction and M&R phase, the environmental burdens are due to the combustion-related emissions from construction machinery usage. Environmental impacts resulting from traffic congestion occurring during M&R interventions are dealt with in the WZ traffic management phase. The consumption-related emissions associated with the operation of each construction equipment were determined by combining the LCI data corresponding to the ecoinvent database process “*machine operation, diesel, >= 74.57 kW, high load factor* / *machine operation, diesel, >= 74.57 kW, high load factor*” with the typical productivity of each operation involved in pavement construction and maintenance activities.

In this section it is worth mentioning that the operating conditions of paving machines were considered the same regardless of the type of asphalt mix considered, i.e. HMA or WMA (with and without). Theoretically, a reduction in the number of roller passes needed to achieve a specified density is expected when WMA is used (Rubio et al., 2012; Zaumanis, 2014). However, there is no accurate and consistent scientific knowledge in the literature on the close relation between the reduction of the compactive effort required, in terms of roller passes, and the enhancement of WMA workability.

### 2.2.3. Transportation of materials phase

The environmental impacts resulting from the transportation of materials are due to the emissions released during the combustion process of the transportation vehicles when performing two-way trips. All materials and mixtures were assumed to be hauled by HDV, and a modified version of the ecoinvent database process “*transport, freight, lorry >32 metric ton, EURO4* / *transport, freight, lorry >32 metric ton, EURO4* / *cut-off, U*” was used to determine the environmental burdens associated with the transportation of materials movements. The original process was modified in order to disregard the inventory corresponding to the construction of the road infrastructure that is considered by the original

1 process. The transportation distances considered for each material and mixture used in this case study  
2 are representative of the French conditions and are shown in Table 4.

3  
4 **Table 4. Transportation distances considered in the case study.**

| Type of material               | One-way trip distance (km) |
|--------------------------------|----------------------------|
| Aggregates                     | 20                         |
| RAP                            | 20                         |
| Binder and bitumen emulsion    | 100                        |
| Asphalt mixtures               | 20                         |
| Emulsifer <sup>a</sup>         | 500                        |
| Hydrochloric acid <sup>a</sup> | 500                        |
| CECABASE <sup>®</sup> additive | 50                         |

5 Notes: <sup>a</sup> Bitumen emulsion component.

#### 6 2.2.4. *Work-zone traffic management phase*

7 This pavement life cycle phase accounts for the marginal FC and emissions released by on-road  
8 vehicles due to traffic perturbations caused by M&R events in relation to those during normal road  
9 operation. The procedure adopted to calculate the environmental burdens arising during this phase was  
10 based on the two-step methodology developed by Santos et al. (2015a, 2015b).

11 First, the COPERTv5.0 air pollutants and GHG emissions model (EMISIA, 2017) was run multiple  
12 times, each considering a different speed in the “Highway” driving mode, to compute a set of FC and  
13 emissions factors representing the French vehicle fleet characteristics per type of vehicle. Next, the FC  
14 and vehicle emissions calculated for the several discrete speed values are used to derive equations that  
15 allow to determine FC and emissions factors representative of the French vehicle fleet as a continuous  
16 function of the speed.

17 Secondly, changes in driving patterns were modelled using the capacity and delay models proposed  
18 by the HCM 2000 (TRB, 2000) to determine several outputs, such as the number of vehicles that  
19 traversed the WZ, the average queue length, the average queue speed in each hour, etc. Each section  
20 where there is a change in driving pattern was considered to be a new road “link”. The characteristics  
21 of each link (length, number of vehicles and average speed) was combined with the equations previously  
22 determined to derive the environmental load of a WZ hour of a given M&R activity. Finally, the  
23 marginal FC and airborne emissions due to the WZ traffic management plan were calculated by  
24 subtracting FC and airborne emissions released during a WZ period from the results of an equivalent  
25 non-WZ period.

#### 26 2.2.5. *Usage phase*

27 The usage phase addresses the pavement’s environmental burden resulting from the interaction of  
28 the pavement with the vehicles, environment and humans throughout its PAP. Among the factors that  
29 have been identified in past research as being worthy of consideration during the usage phase of the  
30 pavement (i.e., pavement-vehicle interaction (PVI), traffic flow, albedo, leachate and runoff,  
31 carbonation and lighting) only the contribution from the PVI, namely that due to the pavement surface  
32 properties (i.e., macrotexture and pavement roughness), was taken into account in this analysis. The  
33 rationale for this decision lies in the fact that the remaining components either do not apply to the  
34 features of the case study under evaluation or lack well established and consistent scientific background.  
35 In order to determine the influence of the pavement surface properties on vehicle FC and tailpipe  
36 emissions, the Swedish National Road and Transport Research Institute (VTI)’s rolling resistance (RR)  
37 model (Hammarström et al., 2012), developed within the European project MIRIAM (Models for  
38 rolling resistance In Road Infrastructure Asset Management systems), was combined with data from the

1 COPERTv5.0 emissions model according to the two-step methodology proposed by Santos et al.  
2 (2015a).

3 In the first step, the VTI's RR model was used to calculate the additional FC due to the vehicles  
4 travelling over the rough pavement surface when compared to the FC of the vehicles travelling over a  
5 smooth surface. Then, instead of using the actual AADT in the COPERTv5.0 emissions model, an  
6 effective AADT ( $AADT_E$ ) was used to relate the effect of pavement surface properties on the FC and  
7 emissions. The  $AADT_E$  for a given macrotexture and roughness at time  $t$ , expressed in terms of the  
8 mean profile depth (MPD) and international roughness index (IRI), respectively, was calculated using  
9 Equation (2).

$$10 \quad AADT_E(t) = AADT(t) \times \sum_{i=0}^{N\_Veh} Veh_i \times \frac{FC_i^{IRI(t),MPD(t)}}{FC_i^{smooth}} \quad (2)$$

11  
12 Where AADT is the annual average daily traffic value,  $N\_Veh$  is the number of types of vehicles (in  
13 this case study it is equal to three, corresponding to passenger cars, rigid HDV and articulated HDV),  
14  $Veh_i$  is the percentage of vehicles of type  $i$  in the AADT,  $FC_i^{IRI(t),MPD(t)}$  is the FC for the type of vehicle  $i$   
15 travelling on a pavement with a specified IRI and MPD at time  $t$ , and  $FC_i^{smooth}$  is the FC of the same  
16 type of vehicle  $i$  travelling along a typical smooth pavement.

17  
18 Estimating the influence of RR on FC and tailpipe emissions requires the prediction of the  
19 progression of the pavement surface properties over the PAP. In this case study, the pavement  
20 performance prediction model of the flexible pavement design method developed by AASHTO (1993)  
21 was adopted to predict the quality of the pavement over time, expressed in terms of PSI (Equation (3)).  
22 This model was posteriorly combined with the expression proposed by Al-Omari and Darter (1994) to  
23 convert the PSI into IRI (Equation (4)). From the conceptual point of view, such conversion does not  
24 seem to represent an obstacle, as roughness is widely recognized as the main contributor to PSI. In turn,  
25 the model proposed by Lorino et al. (2008) was adopted to predict the evolution of the macrotexture  
26 over the PAP (Equation (5)).

$$27 \quad PSI_t = PSI_0 - (4.2 - 2) \times 10^{\left[ \left( \log_{10}(W_{80}_t) - Z_R \times S_0 - 9.36 \times \log_{10}(SN_t + 1) + 0.2 - 2.32 \times \log_{10}(M_R) + 8.07 \right) \times \left( 0.4 + \frac{1094}{(SN_t + 1)^{5.19}} \right) \right]} \quad (3)$$

$$28 \quad IRI_t = -\frac{1}{0.24} \times \ln\left(\frac{PSI_t}{5}\right) \quad (4)$$

$$29 \quad MPD_t = 0.986 - 0.168 \times \ln(age) \quad (5)$$

30 Where  $PSI_t$  is the Present Serviceability Index in year  $t$ ,  $PSI_0$  is the Present Serviceability Index of a  
31 pavement immediately after construction (year 0),  $W_{80}_t$  is the number of 80 kN equivalent single axle  
32 load (ESAL) applications in year  $t$  (million ESAL/lane),  $Z_R$  is the standard normal deviate,  $S_0$  is the  
33 combined standard error of the traffic prediction and performance prediction,  $SN_t$  is the structural  
34 number of a pavement structure in year  $t$ ,  $M_R$  is the sub-grade resilient modulus (pounds per square  
35 inch),  $IRI_t$  is the International Roughness Index (m/km),  $MPD_t$  is the mean profile depth (mm),  $age$   
36 is the age of the surface course (years). In this case study the following parameters values were  
considered: a  $Z_R$  value of -1.282, a  $S_0$  value of 0.45 and a  $SN_0$  value of 5.13.

### 2.2.6. *End-of-life phase*

When a road pavement reaches the end of the PAP, it can be given two main destinations: (1) remain in place, or; (2) be removed. In this case study, it is assumed that the pavement remains in place and undergoes the M&R activity illustrated in Figure 2. The environmental burdens assigned to this phase are due to the materials extraction and mixtures production and the combustion-related emissions from the use of the construction equipment and transportation HDV. The environmental impacts resulting from the traffic disruption occurring during the EOL intervention are dealt with in the WZ traffic management phase.

## 2.3. *Life Cycle Impact assessment*

The life cycle impact assessment (LCIA) stage of the standardized LCA methodology comprises several steps, namely, classification, characterization, normalization, group and weighting (ISO, 2006a). Among these steps, only classification and characterization were undertaken in this study. The normalization, group and weighting are optional, and while they might be useful in translating the impact scores of different impact categories into a more understandable and somehow digestible form (Dahlbo et al., 2013), they also entail a risk of oversimplifying the results. Furthermore, in accordance with ISO 14040 series (ISO, 2006a; ISO, 2006b) no form of numerical, value-based weighting of the indicator results is permitted to be published, if the study is intended to support a comparative assessment to be disclosed to the public.

The calculation of the impact category indicator scores was performed at midpoint level by applying mainly the LCIA method CML 2001 (Guinée et al., 2002). This method was selected because it is the primary base for the construction of the French environmental standards on building construction materials, the NF P 01-010 standard (AFNOR & French Standardisation Agency, 2004). Specifically, the following impact categories were considered: Climate Change (CC), Acidification (AC), Eutrophication (EU), Human toxicity (HT), Terrestrial ecotoxicity (TE), Photochemical oxidation (PO), Stratospheric ozone layer depletion (SOD), Abiotic resources depletion (ARD). Complementarily, the ReCiPe method's impact categories Particulate matter formation (PM) and Water depletion (WD) were also considered (Goedkoop et al., 2013). A time horizon of 100 years was considered for all impacts categories.

In addition, an energy analysis was carried out based on the cumulative energy demand (CED) indicator, computed according to Frischknecht et al. (2007).

Finally, the OpenLCA software version 1.5.0 was used for modelling the processes analyzed in this case study (GreenDelta, 2016).

## 3. **Results and discussion**

### 3.1. *Baseline scenario*

#### 3.1.1. *Total pavement life cycle impacts assessment results*


The comparison between the environmental and energy indicators scores of the six pavement construction and M&R alternatives are illustrated in Figure 3. Table 1 in supplementary materials present their values. Based on LCIA results, one can say that a pavement construction and M&R scenario in which the mixture Foamed WMA, 50%RAP is employed in the wearing course throughout the pavement life cycle is the most environmentally friendly alternative among all the competing solutions, as it was found to present the best environmental performance in all environmental and energy indicators. For instance, for CC its overall impact score totals 1178377 kg CO<sub>2</sub>-eq, for AC 9630 SO<sub>2</sub>-eq, for HT 600713 kg 1,4-DCB-eq, for PO 543 kg ethylene-eq, and for ARD 27452 kg antimony-eq. These values mean a reduction of 6%, 7%, 5%, 8% and 9%, respectively, in relation to the impact scores associated with the use of the mixture HMA, 0%RAP.




1 Indeed, the use of the mixture HMA, 0%RAP in the wearing course of a pavement throughout its  
 2 life cycle is, in general, the most environmentally damaging alternative among all the competing  
 3 solutions, as it was found to exhibit the worst environmental performance in 9 of the 12 environmental  
 4 and energy indicators. The exceptions to the “12 of the 12” were observed for the impact categories TE,  
 5 WD and renewable CED in which the alternative WMA- CECABASE<sup>®</sup>, 0% RAP denoted the most  
 6 expressive scores (i.e. 2035 kg 1.4-DCB-eq, 4123 m<sup>3</sup> and 625501 MJ), followed by its recycling-based  
 7 counterpart, i.e. the mixture WMA- CECABASE<sup>®</sup>, 50% RAP with impact scores equal to 2016 kg 1.4-  
 8 DCB-eq, 3936 m<sup>3</sup> and 591512 MJ, respectively. Such results, which in the case of the mixture WMA-  
 9 CECABASE<sup>®</sup>, 0% RAP represent an increase of 233%, 70% and 19% relatively to those of the mixture  
 10 HMA, 0%RAP, are explained by the process “*market for fatty acid / fatty acid / cut-off, S - GLO*”, which  
 11 with contributions greater than 71% and 41%, respectively for the impact categories TE and WD, was  
 12 found to be main driver of such categories. Also, it was the responsible for the notorious consumption  
 13 of biomass energy that is the root cause of the greater consumption of renewable energy. Similar  
 14 contributions were found in the case of its recycling-based counterpart (i.e., the mixture WMA-  
 15 CECABASE<sup>®</sup>, 50% RAP).


16 On comparing pavement construction and M&R alternatives employing in the wearing course  
 17 HMA or WMA mixtures without the addition of RAP, it was observed that the overall life cycle impacts  
 18 of the alternatives using WMA mixtures were, in general, reduced by no more than 2% (WMA-  
 19 CECABASE<sup>®</sup>, 0% RAP) and 3% (Foamed WMA, 0%RAP). These tiny benefits agree well with the  
 20 findings reported by Vidal et al. (2013), although the type of WMA analysed in that study was different  
 21 from those considered in the present study.

22 In addition, when comparing mixtures with a null content of RAP with their recycling counterpart  
 23 (i.e. 50% RAP), it was observed that the life cycle environmental benefits mentioned above rose to  
 24 values that can be as high as 9%. That is the case of the mixtures HMA, 50%RAP and WMA-  
 25 CECABASE<sup>®</sup>, 50% RAP for the impact categories ARD and SOD. Indeed, for those impact categories  
 26 all the mixtures that do not contain RAP and those that contain RAP denote similar scores. In turn, the  
 27 lowest life cycle environmental benefits are registered by the mixtures WMA- CECABASE<sup>®</sup>, 50% RAP  
 28 and Foamed WMA, 50%RAP for the impact category TE (1% and 2%, respectively).  
 29

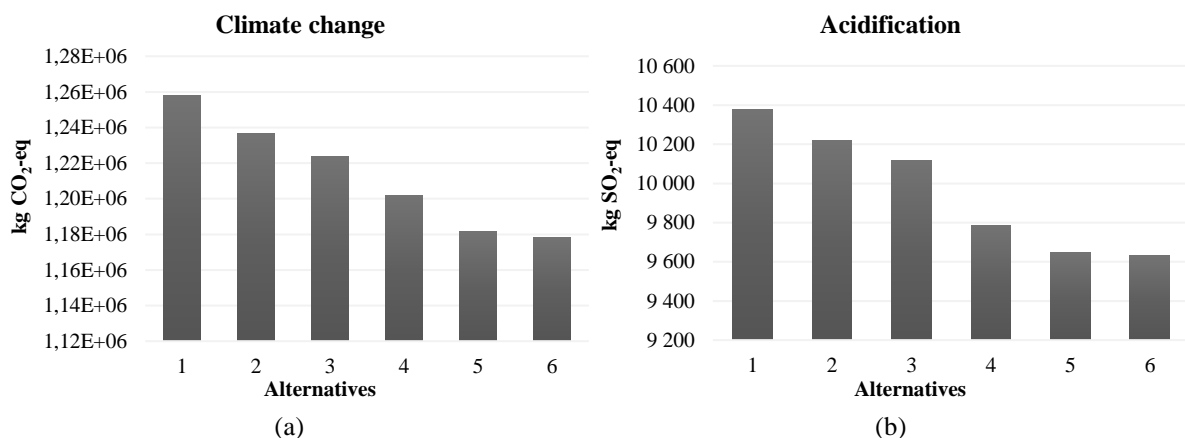


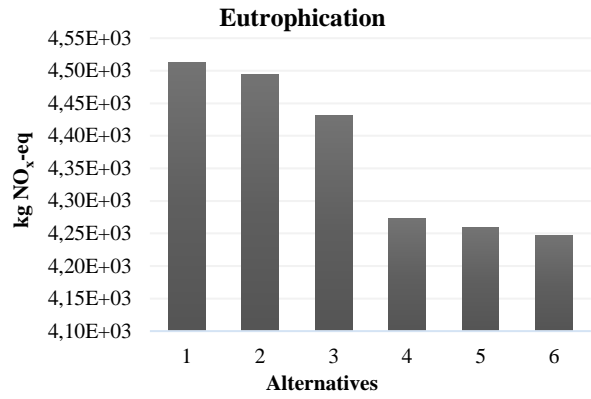


(c)

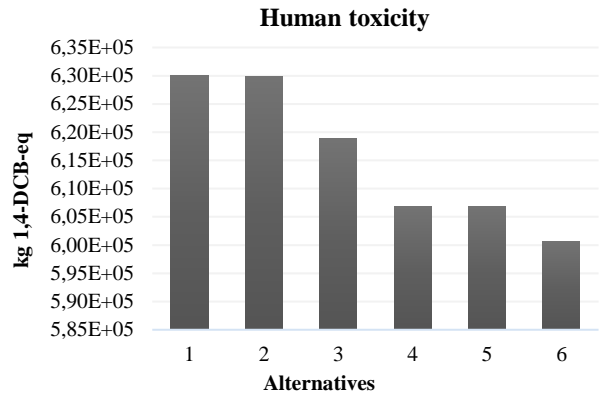


(d)

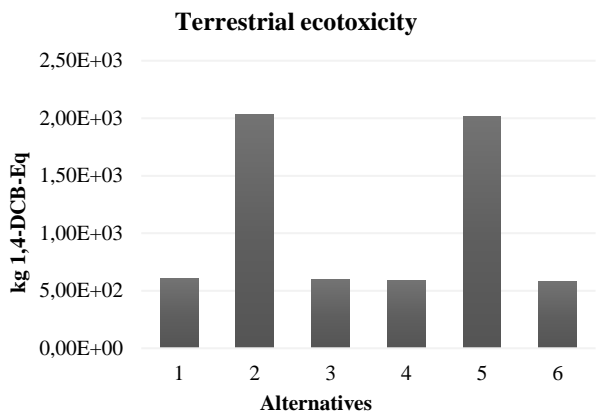


(e)

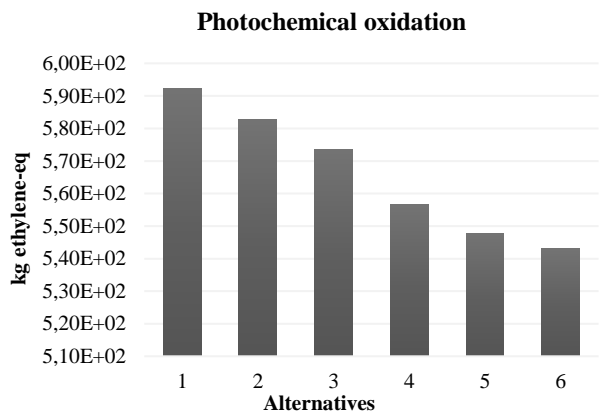


(f)

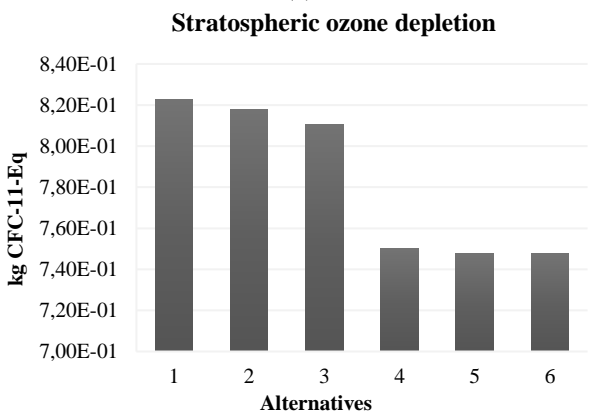


(g)

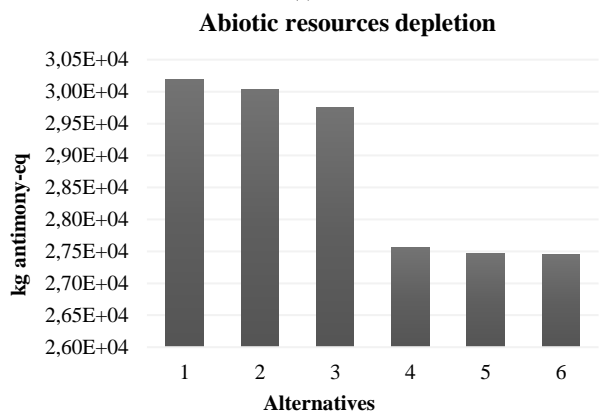


(h)

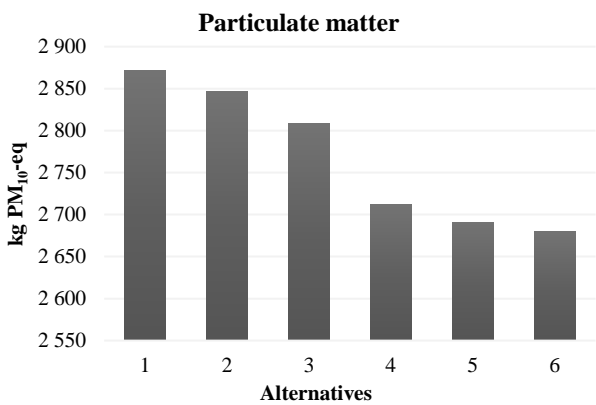

(i)

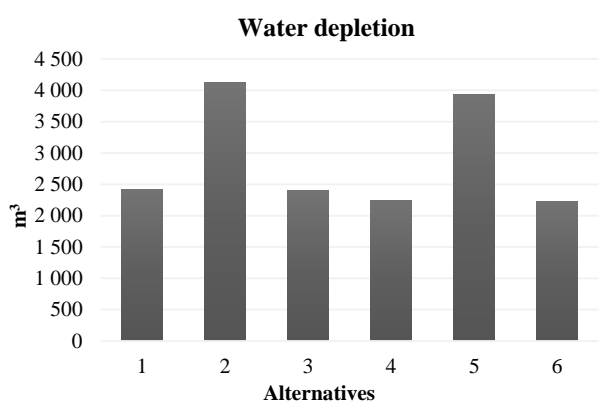

(j)

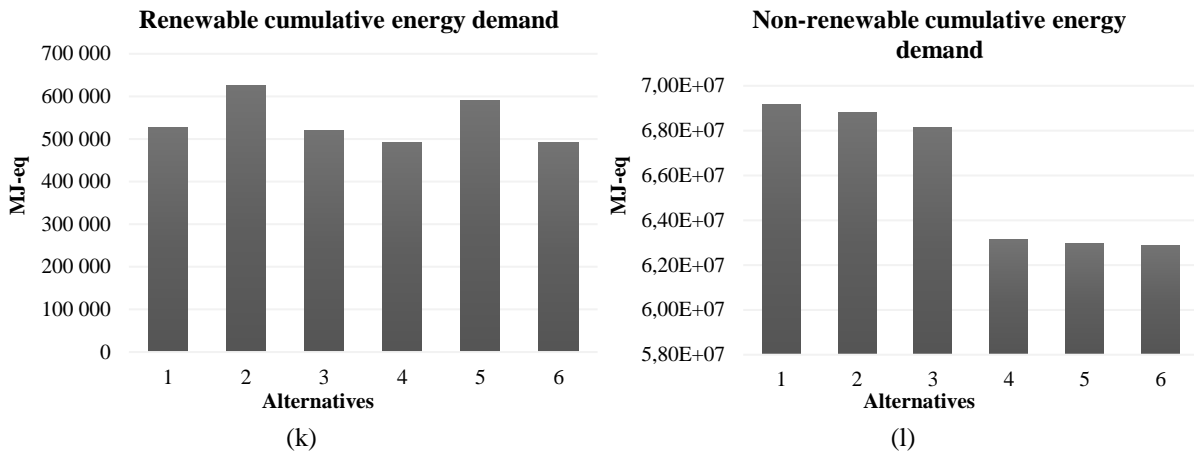



1 **Figure 3. Life cycle impact assessment results. Key: Alternative 1: HMA, 0%RAP; Alternative 2: WMA-**  
 2 **CECABASE<sup>®</sup>, 0%RAP; Alternative 3: Foamed WMA, 0%RAP; Alternative 4: HMA, 50%RAP;**  
 3 **Alternative 5: WMA- CECABASE<sup>®</sup>, 50%RAP; Alternative 6: Foamed WMA, 50%RAP.**

4 3.1.2. *Process contribution analysis*

5 Figure 4 displays the contribution of the processes to the impact categories considered for all  
 6 alternatives being compared. Overall, the environmental impacts are driven predominantly by the  
 7 processes bitumen production and asphalt mixtures manufacturing. This general pattern is observed not  
 8 only for all impact categories but also across all the alternatives. The share of the process bitumen  
 9 production can be as high as 83% (SOD score for the alternatives WMA- CECABASE<sup>®</sup>, 0% RAP and  
 10 Foamed WMA, 0%RAP), whereas the highest contribution given by the asphalt mixtures manufacturing  
 11 (around 57%) is observed in the impact category TE for the alternative conventional HMA, 0%RAP.  
 12 The market for asphalt mixing plant and gravel production are other processes whose contributions  
 13 cannot be neglected, although their maximum share does not go beyond 35% (HT score for the  
 14 alternative conventional HMA, 0%RAP) and 25% (WD score for the alternative Foamed WMA,  
 15 0%RAP), respectively. In turn, the contributions of the transportation of materials and construction  
 16 machinery operation are relatively reduced, under 7% (EU score for the alternatives conventional HMA,  
 17 0%RAP, WMA- CECABASE<sup>®</sup>, 0% RAP, Foamed WMA, 0% RAP and WMA- CECABASE<sup>®</sup>, 50%  
 18 RAP) and 8% (EU score for the alternative WMA- CECABASE<sup>®</sup>, 50% RAP), respectively.

19 Finally, it is worth mentioning that the length of the bars corresponding to the mixtures WMA-  
 20 CECABASE<sup>®</sup>, 0% RAP and WMA- CECABASE<sup>®</sup>, 50% RAP for the impact categories TE and WD  
 21 prove what was said in the previous section regarding the preponderance of the contribution given by  
 22 the process “market for fatty acid | fatty acid | cut-off, S - GLO” for the scores of those impact categories.  
 23

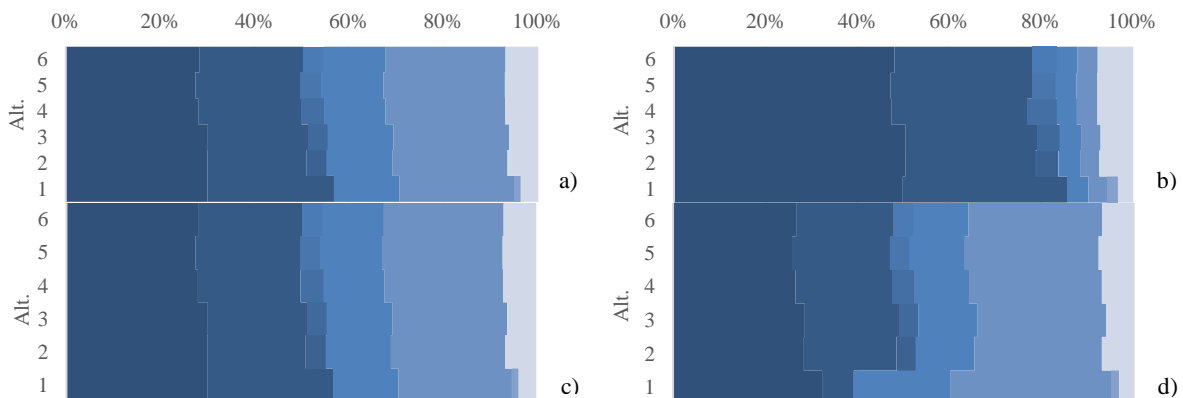

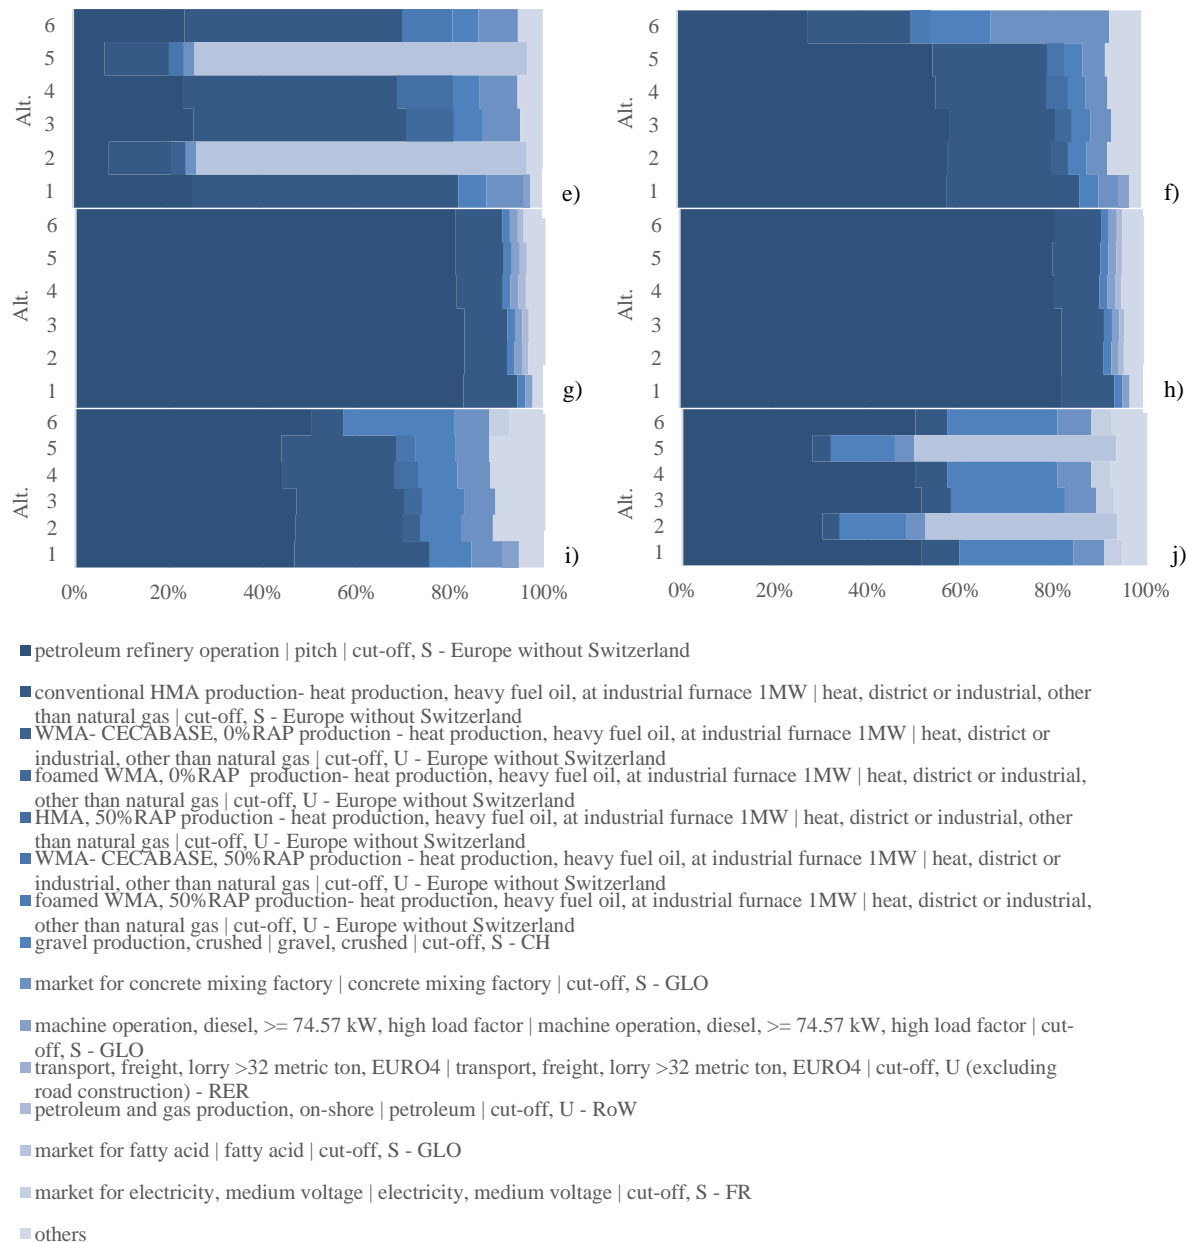


1 **Figure 4. Contribution analysis by process: a) climate change; b) acidification; c) eutrophication; d) human**  
 2 **toxicity; e) terrestrial ecotoxicity; f) photochemical oxidation; g) stratospheric ozone depletion; h) abiotic**  
 3 **resources depletion; i)- particulate matter; j) water depletion. Key: Alternative 1: HMA, 0%RAP;**  
 4 **Alternative 2: WMA- CECABASE®, 0%RAP; Alternative 3: Foamed WMA, 0%RAP; Alternative 4:**  
 5 **HMA, 50%RAP; Alternative 5: WMA- CECABASE®, 50%RAP; Alternative 6: Foamed WMA, 50%RAP.**


### 6 3.1.3. Pavement life cycle phase contribution analysis

7 Figure 5 presents the contribution of each of the pavement life cycle phases to the 12 impact and  
 8 energy indicators considered and for each of the pavement construction and M&R alternatives studied.  
 9 The environmental performance of all alternatives for almost all impact and energy indicators are  
 10 mainly driven by the phases related to the construction of the initial pavement structure, which  
 11 comprises the materials extraction and production, the construction machinery operation and the  
 12 transportation of the materials and mixtures. Its share varies between 29% and 57% for the indicator  
 13 TE. The exception to the construction phase's dominance is observed in the TE indicator for the  
 14 alternatives WMA- CECABASE®, 0% RAP and WMA- CECABASE®, 50% RAP, where the  
 15 maintenance phase is the main contributor. The root cause of this outcome is the preponderance of the

process “market for fatty acid / fatty acid / cut-off, S - GLO” in driving the environmental burdens of those alternatives with respect to the impact categories TE and WD, along with the fact that the total mass of those mixtures applied in all maintenance activities performed throughout the pavement life cycle is greater than that employed in the construction of the initial pavement structure. If the TE and WD indicators were not taken into account, then the construction phase would always be the main contributor for the remaining indicators with a minimum share not inferior to 49%, followed by the maintenance and EOL phases.

Another noteworthy result emerging from the analysis of Figure 5 pertains to the almost consensual residual contribution given by the WZ traffic management and usage phases to all impact and energy indicators. Furthermore, in the usage phase the relative contributions are not only approximately 0%, but also negative, meaning that this phase plays a beneficial role for the environment. In the case of the WZ traffic management phase such outcome is entirely explained by the reduced traffic value carried by the road pavement throughout its life cycle, which is not enough to originate congestion when an M&R intervention is performed. As far as the usage phase is concerned, in addition to the low traffic volume, the explanation also lays on the way the pavement roughness and macrotexture impact RR and how such pavement surface properties evolve over time. In the VTI’s RR model, while an increase of pavement roughness and macrotexture leads to an increase of the RR, and thus the vehicle’s fuel consumption, the absolute effect of macrotexture is, in general, greater than that of roughness (Bryce et al., 2014). Given that in this case study the pavement macrotexture is expected to decrease over time according to Lorino et al.’s model, its effect offset that of the roughness, notwithstanding the fact that the value of latter property is expected to increase throughout the pavement life cycle. Therefore, due to the combined effects of the aforementioned surface properties on vehicle’s fuel economy and their evolution over the PAP, the usage phase turns out to be environmentally advantageous.

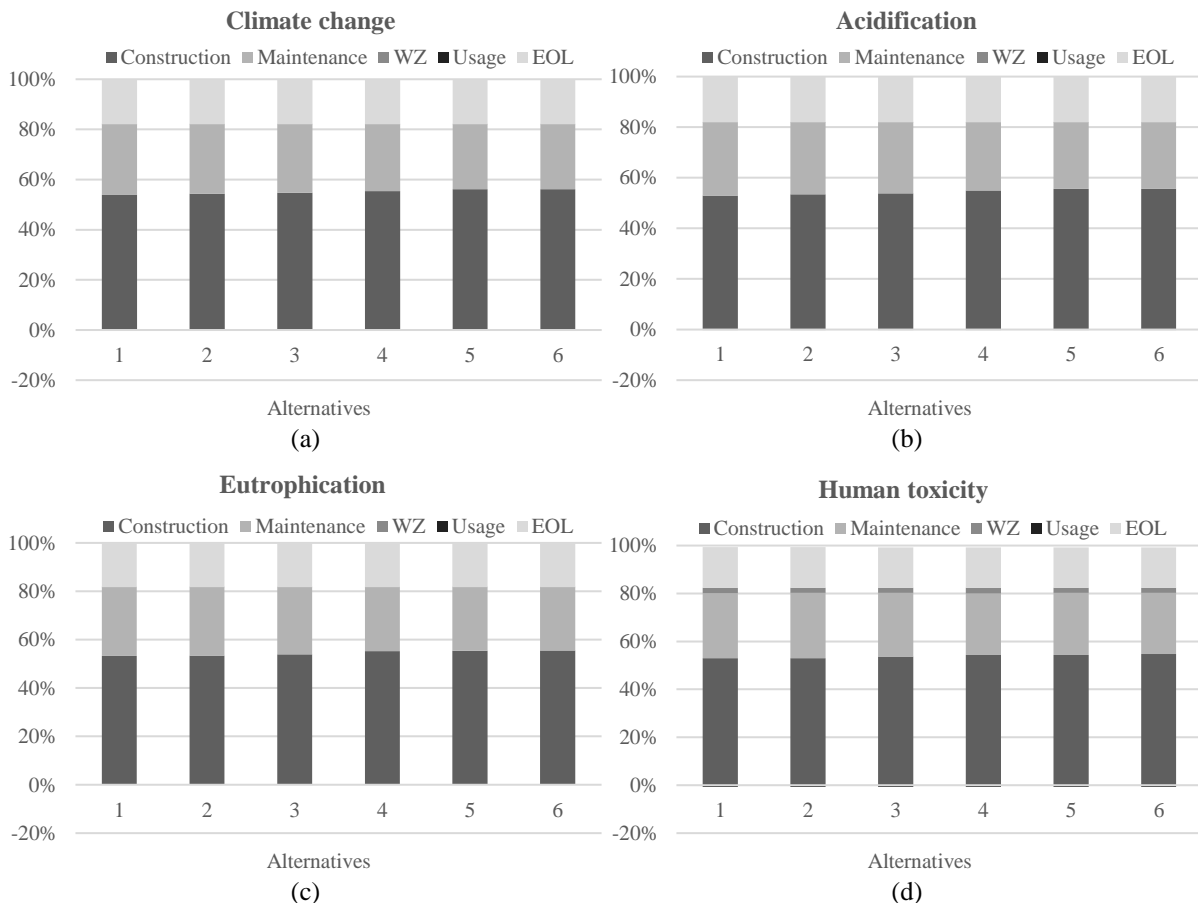

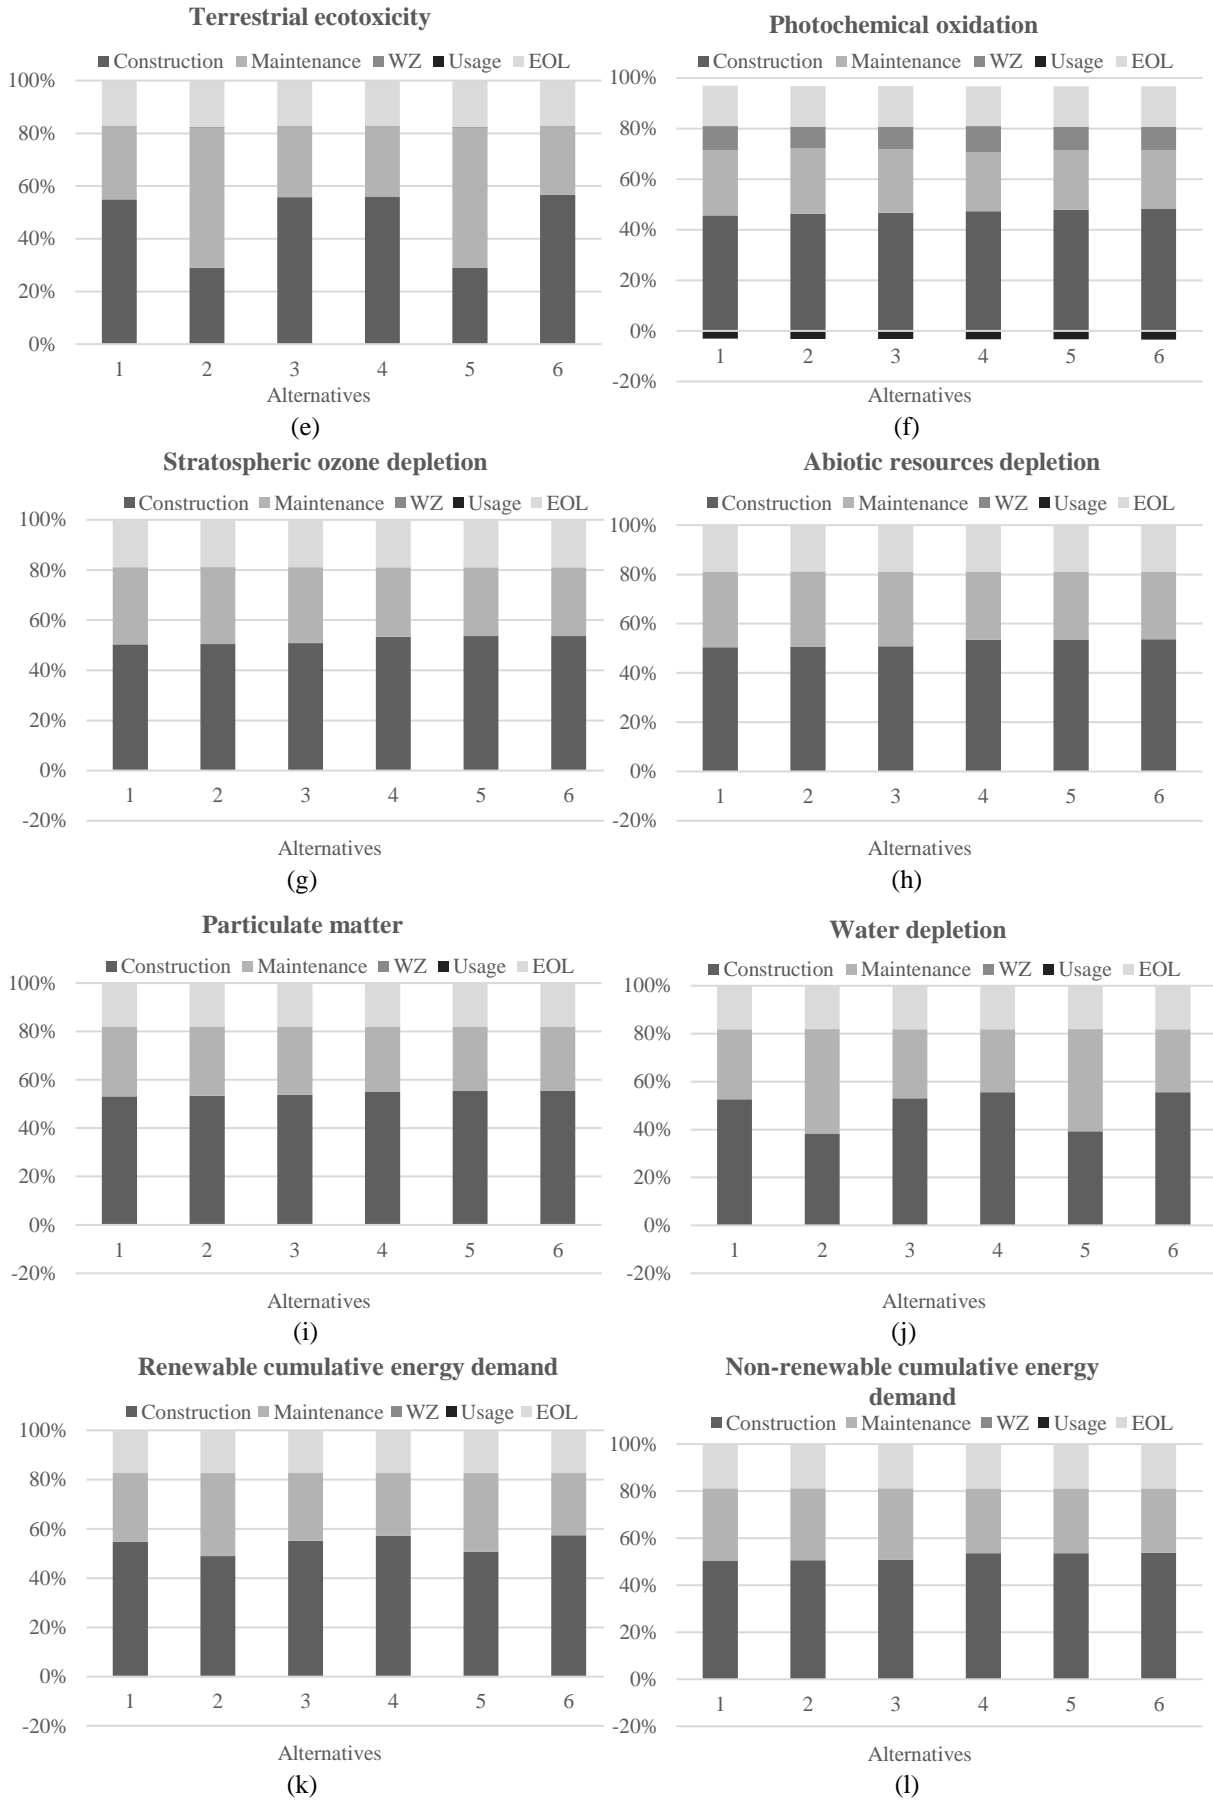

1 **Figure 5. Contribution analysis by pavement life cycle phase: a) climate change; b) acidification; c)**  
2 **eutrophication; d) human toxicity; e) terrestrial ecotoxicity; f) photochemical oxidation; g) stratospheric**  
3 **ozone depletion; h) abiotic resources depletion; i) particulate matter; j) water depletion; k) renewable**  
4 **cumulative energy demand; l) non-renewable cumulative energy demand. Key: Alternative 1: HMA,**  
5 **0%RAP; Alternative 2: WMA- CECABASE<sup>®</sup>, 0%RAP; Alternative 3: Foamed WMA, 0%RAP;**  
6 **Alternative 4: HMA, 50%RAP; Alternative 5: WMA- CECABASE<sup>®</sup>, 50%RAP; Alternative 6: Foamed**  
7 **WMA, 50%RAP.**

### 8 **3.2. Scenario analysis**


9 In order to assess the robustness of the results presented in the previous sub-section to changes in  
10 the methodological assumptions, a scenario analysis was performed by considering two alternative  
11 scenarios. In the first one, hereafter named AS1, it was assumed that the asphalt plant is run by natural  
12 gas rather than by HFO. This is a plausible scenario that stands the best chance of becoming the actual  
13 and near-term future practice, thereby replacing the baseline scenario, as new asphalt plants are  
14 increasingly switching to natural gas because of its general lower price and cleaner-burning properties.  
15 In the second one, hereafter named AS2, it was assumed that the road pavement structure is dismantled  
16 at the EOL and the debris transported to an asphalt plant where they will undergo the required  
17 processing operations to be considered as RAP. The allocation of the environmental impacts was made  
18 in accordance with the considerations underlying to the “cut-off” method described in subsection 2.1.2.  
19 The reasoning for the consideration of this alternative lays on the fact that it is commonly considered  
20 in the literature as the fate to be given to a road pavement when it reaches the end of its lifetime (Van  
21 Dam et al., 2015). Another reason backing the choice of the alternative scenarios pertains to the fact  
22 that they evolve directly the pavement life cycle phases driving the global environmental performance  
23 of the system being analysed.

24 Figures 5 displays for each alternative the relative variation of the LCIA results in relation to the  
25 baseline scenario. They should be understood as follows: positive relative numbers mean that the  
26 alternative scenarios improve the LCIA results in relation to those associated with the baseline scenario  
27 while negative numbers represent a worsening of the environmental profile. The results show an almost  
28 unanimous reduction in all impacts and energy indicators for both alternative scenarios regardless the  
29 pavement construction and M&R alternative studied. Overall, AS2 leads to a uniform reduction of the  
30 scores (13-18%) of all impact categories across all alternatives being compared. In turn, the  
31 consequences resulting from considering the AS1 depend to a great extent on the impact category. The  
32 most expressive improvements in the environmental profiles are observed in the TE indicator (57%) for  
33 the alternative HMA, 50%RAP, while the most feeble improvements are observed in the ARD indicator  
34 (slightly lower 1%) for the alternative Foamed WMA, 0%RAP.

35 Notwithstanding the overall environmental benefits that can be achieved with both alternative  
36 scenarios, there is, however, an exception. It was observed in the alternative scenario AS1 for the energy  
37 indicator R-CED. This scenario increases the aforementioned indicator by 2-3% across the six  
38 alternatives, though it leads to a reduction of the total CED. The latter result is far more important than  
39 the consideration of the former isolatedly, as its explanation lays on the reduction of the NR-CED.

40 When comparing the extent to which the alternative scenarios affects the variation of the scores of  
41 a given impact category across the alternatives being compares, Figure 6 shows that AS1 originates  
42 environmental profiles that are slightly more prone to vary in relation to the baseline scenario, than  
43 those associated with the AS2. Also, among the six alternatives the greatest reductions in the  
44 environmental impacts scores are obtained for the alternative HMA, 50%RAP. Moreover, the  
45 environmental performances of the alternatives incorporating RAP seem to be less susceptible to  
46 variations when the AS2 is assumed to be implemented comparatively to the scenario in which the  
47 pavement structure is supposed to be dismantled at the end of its lifetime (AS2).

1 Finally, the results of the scenario analysis indicate that shifting the type of fuel consumed by  
 2 asphalt plants from HFO to natural gas offers considerable potential environmental benefits and a more  
 3 trustworthy option, as it refers to a decision made in the present with immediate consequences, whereas  
 4 those associated with the AS2 depend on a decision which will be made far in the future, and thereby  
 5 entails a great deal of uncertainty.  
 6

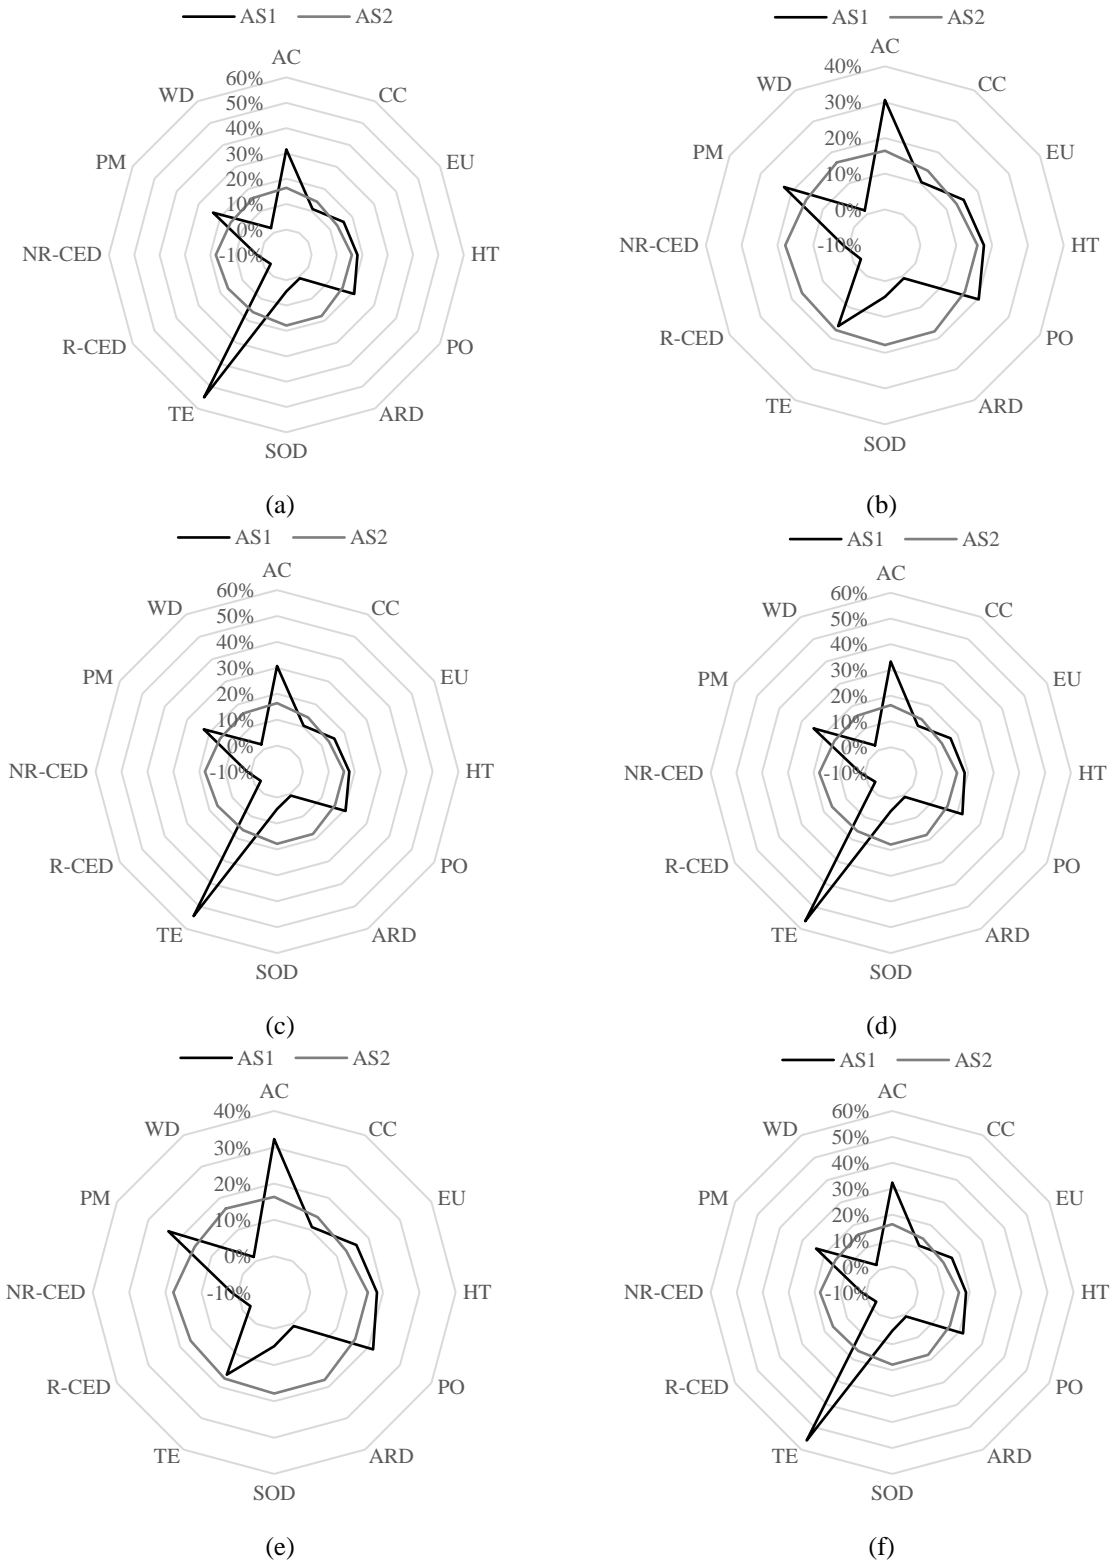

7 **Figure 6. Relative variation of the LCIA results in relation to the baseline scenario: a) Alternative 1: HMA,**  
 8 **0%RAP; b) Alternative 2: WMA- CECABASE®, 0%RAP; c) Alternative 3: Foamed WMA, 0%RAP; d)**



1 **Alternative 4: HMA, 50%RAP; e) Alternative 5: WMA- CECABASE<sup>®</sup>, 50%RAP; f) Alternative 6: Foamed**  
2 **WMA, 50%RAP. Acronyms: AS1- alternative scenario 1; AS2- alternative scenario 2; CC- Climate**  
3 **Change; AC- Acidification; EU- Eutrophication; HT- Human toxicity; TE- Terrestrial ecotoxicity; PO-**  
4 **Photochemical oxidation; SOD- Stratospheric ozone layer depletion; ARD- Abiotic resources depletion;**  
5 **PM- Particulate matter formation; WD- Water depletion; NR-CED- Non-renewable cumulative energy**  
6 **demand; R-CED- Renewable cumulative energy demand.**

#### 7 **4. Summary and conclusions**

8 In this paper, the results of a comprehensive process-based LCA of French road pavement sections  
9 incorporating alternatively two different WMA technologies, with and without RAP content, were  
10 presented and compared with those in which conventional HMA mixtures, also with and without RAP  
11 content, were adopted. The life cycle of the road pavement sections was divided into six main phases:  
12 (1) materials extraction and mixtures production; (2) construction and M&R; (3) transportation of  
13 materials; (4) WZ traffic management; (5) usage; and (6) EOL. The LCI of inputs and outputs associated  
14 with the processes considered by the several pavement life cycle phases was determined by combining  
15 primary data, representing the current French practices and conditions, with secondary data taken  
16 primarily from the ecoinvent database version 3.2 and complemented with publicly available reports.  
17 Complementary, an energy balance model was developed to account for the energy required to produce  
18 the several mixtures studied, as well as the airborne emissions released during their production, as a  
19 function of the mixing temperature and the features of the mixtures components. The CML 2001 impact  
20 assessment method along with the CED indicator were adopted to characterize the environmental  
21 performance of the following asphalt mixtures: (1) conventional HMA, 0% RAP; (2) WMA-  
22 CECABASE<sup>®</sup>, 0% RAP; (3) Foamed WMA, 0% RAP; (4) HMA, 50% RAP; (5) WMA- CECABASE<sup>®</sup>,  
23 50% RAP; and (6) Foamed WMA, 50% RAP.

24 The LCIA results of the case study showed that, for the mixtures studied and assumptions  
25 performed, the pavement construction and M&R scenario in which the mixture Foamed WMA, 50%  
26 RAP is employed in the wearing course throughout the pavement life cycle is the most environmentally  
27 friendly alternative among all the competing solutions. Regarding the results referring to the relative  
28 contribution of the several processes included in the systems boundaries, it was shown that, overall, the  
29 production of the bitumen is the main responsible for the life cycle environmental burdens of the  
30 systems studied. Moreover, when comparing the contribution given by the several pavement life cycle  
31 phases, the materials extraction and mixtures production was found to be the phase that plays the most  
32 important role in driving the life cycle environmental performance of the road pavement sections  
33 analysed. Finally, the results of a scenario analysis showed that the life cycle environmental impacts  
34 could be reduced if the asphalt plant was fueled by natural gas, or if the pavement structure was  
35 dismantled at the end of its lifetime and the debris recycled.

#### 36 **5. Acknowledgements and disclaimer**

37 The research presented in this paper was carried out as part of the Marie Curie Initial Training  
38 Network (ITN) action, FP7-PEOPLE-2013-ITN. This project has received funding from the European  
39 Union's Seventh Framework Program for research, technological development and demonstration  
40 under grant agreement number 607524.

41 The contents of this paper reflect the views of the authors, who are responsible for the facts and  
42 the accuracy of the data presented. Any inclusion of manufacturer names, trade names, or trademarks  
43 is for identification purposes only and is not to be considered an endorsement. Moreover, this paper  
44 does not constitute a standard, specification, or regulation.

#### 45 **6. References**

- 1 AFNOR, French Standardisation Agency, 2004. Environmental Quality of Construction Products -  
2 Environmental and Health Declaration of Construction Products. AFNOR. 47pp.
- 3 Al-Omari, B., Darter, M., 1994. Relationships between international roughness index and present  
4 serviceability rating. *Transp. Res. Rec. J. Transp. Res. Board.* 1435, 130-136.
- 5 American Association of State Highway and Transportation Officials (AASHTO), 1993. Guide for  
6 design of pavement structures. 4<sup>th</sup> ed. Washington, DC.
- 7 Almeida-Costa, A., Benta, A., 2016. Economic and environmental impact study of warm mix asphalt  
8 compared to hot mix asphalt. *J Clean Prod.* 112, 2308-2317.  
9 <http://dx.doi.org/10.1016/j.jclepro.2015.10.077>.
- 10 Aurangzeb, Q., Al-Qadi, I., Ozer, H. and Yang, R., 2014. Hybrid life cycle assessment for asphalt  
11 mixtures with high RAP content. *Resour. Conserv. Recycl.* 83, 77-86.  
12 <http://dx.doi.org/10.1016/j.resconrec.2013.12.004>.
- 13 Bryce, J., Santos, J., Flintsch, G., Katicha, S., McGhee, K., Ferreira, A., 2014. Analysis of rolling  
14 resistance models to analyze vehicle fuel consumption as a function of pavement properties.  
15 Proceedings of the 3<sup>rd</sup> International Symposium on Asphalt Pavements and Environment, in Asphalt  
16 Pavements, Y. Richard Kim, CRC Press 2014, 263-273, Print ISBN: 978-1-138-02693-3, eBook  
17 ISBN: 978-1-315-73675-4, DOI: 10.1201/b17219-39, Raleigh, North Carolina, USA.
- 18 D'Angelo, J., Harm, E., Bartoszek, J., Baumgardner, G., Corrigan, M., Cowser, J., Harman, T.,  
19 Jamshidi, M., Jones, W., Newcomb, D., Prowell, B., Sines, R., Yeaton, B., 2008. Warm-mix  
20 Asphalt: European Practice. Report No. FHWA/PL-08/007, Federal Highway Administration,  
21 Washington, DC. <https://international.fhwa.dot.gov/pubs/pl08007/pl08007.pdf>.
- 22 Dahlbo, H., Koskela, S., Pihkola, H., Nors, M., Federlay, M., Seppälä, J., 2013. Comparison of different  
23 normalised LCIA results and their feasibility in communication. *Int J Life Cycle Assess.* 18, 850-  
24 860. <http://dx.doi.org/10.1007/s11367-012-0498-4>.
- 25 EN, 2013. EN 15804+A1 Sustainability of construction works - Environmental product declarations -  
26 Core rules for the product category of construction products.
- 27 EMISIA, 2017. EMISIA. Copert v5. <http://emisiam.com/products/copert>.
- 28 Eurobitume, 2011. Life cycle inventory: bitumen. Eurobitume.
- 29 European Commission, Joint Research Center - Institute for Environment and Sustainability (EC, JRC  
30 - IES), 2010. International reference life cycle data system (ILCD) handbook - general guide for  
31 life cycle assessment - detailed guidance. First edition March 2010. EUR 24708 EN. Luxembourg:  
32 Publications Office of the European Union.
- 33 Federal Highway Administration (FHWA), 2016. Strategies for improving the sustainability of asphalt  
34 pavements. Tech brief. Report No. FHWA-HIF-16-012. Federal Highway Administration,  
35 Washington, DC. <https://www.fhwa.dot.gov/pavement/sustainability/hif16012.pdf>.
- 36 Frischknecht, R., Jungbluth, N., Althaus, H.-J., Bauer, C., Doka, G., Dones, R., Hirschler, R., Hellweg,  
37 S., Humbert, S., Köllner, T., Loerincik, Y., Margni, M., Nemecek T., 2007. Implementation of Life  
38 Cycle Impact Assessment Methods.ecoinvent report No. 3, v2.0. Swiss Centre for Life Cycle  
39 Inventories, Dübendorf.
- 40 Giani, M., Dotelli, G., Brandini, N., Zampori, L., 2015. Comparative life cycle assessment of asphalt  
41 pavements using reclaimed asphalt, warm mix technology and cold in-place recycling. *Resour.*  
42 *Conserv. Recycl.* 104, 224-238. <http://dx.doi.org/10.1016/j.resconrec.2015.08.006>.
- 43 Goedkoop, M., Heijungs, R., Huijbregts, M., De Schryver, A., Struijs, J., van Zelm, R., 2013. ReCiPe  
44 2008- a life cycle impact assessment method which comprises harmonized category indicators at  
45 the midpoint and the endpoint level. Ministerie van VROM, Den Haag.
- 46 Guinee, J., Gorree, M., Heijungs, R., Huppes, G., Kleijn, R., de Koning, A., van Oers, L., Sleswijk,  
47 A., Suh, S., Udo de Haes, H., de Bruijn, H., van Duin, R., Huijbregts, M., 2002. Handbook on

1 lifecycle assessment. Operational guide to the ISO standards. I: LCA in perspective. IIa: guide. IIb:  
2 operational annex. III: scientific background. Kluwer Academic Publishers, Dordrecht.

3 Hammarström, U., Eriksson, J., Karlsson, R., Yahya, M.-R., 2012. A rolling resistance model, a fuel  
4 consumption model and the traffic energy saving potential from changed road surface condition.  
5 VTI Report 748A. The Swedish National Road and Transport Research Institute.

6 Hamzah, M., Jamshidi, A., Shahada, Z., 2010. Evaluation of the potential of Sasobit® to reduce required  
7 heat energy and CO2 emission in the asphalt industry. *J Clean Prod.* 18, 1859-1865.  
8 <http://dx.doi.org/10.1016/j.jclepro.2010.08.002>.

9 Harvey, J., Meijer, J., Ozer, H., Al-Qadi, I., Saboori, A., Kendall, A., 2016. Pavement Life-Cycle  
10 Assessment Framework. Report N° FHWA-HIF-16-014, Federal Highway Administration,  
11 Washington, DC. <https://www.fhwa.dot.gov/pavement/sustainability/hif16014.pdf>

12 IEA, 2005. Energy statistics manual. France: IED Publications.

13 International Standard Organization (ISO), 2006a. ISO 14040: 2006. International Standard ISO 14040:  
14 Environmental Management - Life Cycle Assessment: Principles and Framework, October. Geneva  
15 (Switzerland). International Organization for Standardization.

16 International Standard Organization (ISO), 2006b. ISO 14044:2006. International Standard ISO 14044:  
17 Environmental Management - Life Cycle Assessment: Requirements and Guidelines, October.  
18 Geneva (Switzerland). International Organization for Standardization.

19 Jones, W., 2004. Warm mix asphalt-a state-of-the-art review. Australian Asphalt Pavement Association  
20 Advisory Note, 17.

21 Jullien, A., Dauvergne, M., Cerezo, V., 2014. Environmental assessment of road construction and  
22 maintenance policies using LCA. *Transp. Res. Part Transp. Environ.* 29, 56-65.  
23 <http://dx.doi.org/10.1016/j.trd.2014.03.006>.

24 Jullien, A., Cerezo, V., Keijzer, E., Lòpez, A.-M., 2015. ECOLABEL. Deliverable D1.4: benchmarking  
25 exercise to assess the set of proposed indicators in diverse road case studies. 1-106.

26 Kristjánssdóttir, Ó., Muench, S., Michael, L., Burke, G., 2007. Assessing potential for warm-mix asphalt  
27 technology adoption. *Transp. Res. Rec. J. Transp. Res. Board.* 2040, 91-99.  
28 <http://dx.doi.org/10.3141/2040-10>.

29 Lo Presti, D., Airey, G., Rubio, M., Marsac, P., 2017. SUP&R ITN: an international training network  
30 on sustainable pavements and railways, in: Dell'Acqua, G. and Wegman, F. (Eds), *Transport  
31 Infrastructure and Systems: Proceedings of the Aiiit International Congress on Transport  
32 Infrastructure and Systems (TIS 2017)*, Rome, Italy, 10-12 April 2017, CRC Press/Balkema P.O.  
33 Box 11320, 2301 EH Leiden, The Netherlands CRC Press/Balkema 2017, pp. 47-54, Print ISBN:  
34 978-1-138-03009-1. <https://doi.org/10.1201/9781315281896-9>.

35 Lorino, T., Lepert, P., Giacobi, C., Layerle, E., 2008. Pavement surface characteristics evolution. SURF  
36 2008, France. 1-17.

37 Matthews, H., Hendrickson, C., Matthews, D., 2015. Life cycle assessment: quantitative approaches for  
38 decisions that matter. Green Design Institute, Carnegie Mellon University, Pittsburgh.

39 Mohammad, L., Hassan, M., Vallabhu, B., Kabir, M., 2015. Louisiana's experience with WMA  
40 technologies: mechanistic, environmental, and economic analysis. *J Mater Civil Eng.* 27, 04014185.  
41 [http://dx.doi.org/10.1061/\(ASCE\)MT.1943-5533.0001143](http://dx.doi.org/10.1061/(ASCE)MT.1943-5533.0001143).

42 GreenDelta, 2016. Open LCA. Available at: <http://www.openlca.org>.

43 Rodríguez-Alloza, A., Malik, A., Lenzen, M., Gallego, J., 2015. Hybrid input-output life cycle  
44 assessment of warm mix asphalt mixtures. *J Clean Prod.* 90, 171-182.  
45 <http://dx.doi.org/10.1016/j.jclepro.2014.11.035>.

46 Rubio, M., Moreno, F., Martínez-Echevarría, M., Martínez, G. and Vázquez, J., 2013. Comparative  
47 analysis of emissions from the manufacture and use of hot and half-warm mix asphalt. *J Clean Prod.*  
48 41, 1-6. <http://dx.doi.org/10.1016/j.jclepro.2012.09.036>.

- 1 Santos, J., Flintsch, G., Ferreira, A., 2017. Environmental and economic assessment of pavement  
2 construction and management practices for enhancing pavement sustainability. *Resour. Conserv.  
3 Recycl.* 116, 15-31. <http://dx.doi.org/10.1016/j.resconrec.2016.08.025>.
- 4 Santos, J., Ferreira, A., Flintsch, G., 2015a. A life cycle assessment model for pavement management:  
5 methodology and computational framework. *Int. J. Pavement Eng.* 16, 268-286.  
6 <http://dx.doi.org/10.1080/10298436.2014.942861>.
- 7 Santos, J., Bryce, J., Flintsch, G., Ferreira, A., Diefenderfer, B., 2015b. A life cycle assessment of in-  
8 place recycling and conventional pavement construction and maintenance practices. *Struct.  
9 Infrastruct. Eng.: Maint. Manag. Life-Cycle Des. Perform.* 11, 1199-1217.  
10 <http://dx.doi.org/10.1080/15732479.2014.945095>.
- 11 Santucci, L., 2010. Warm mix asphalt hits the road. *Pavement Technology Update*, The University of  
12 California Pavement Research Center. Technology Transfer Program, 2(1), 1-12.  
13 [http://www.techtransfer.berkeley.edu/sites/default/files/pave-tech/prc\\_update\\_vol2\\_no1.pdf](http://www.techtransfer.berkeley.edu/sites/default/files/pave-tech/prc_update_vol2_no1.pdf).
- 14 Schrijvers, D., Loubet, P., Sonnemann, G., 2016a. Critical review of guidelines against a systematic  
15 framework with regard to consistency on allocation procedures for recycling in LCA. *Int J Life  
16 Cycle Assess.* 21, 994-1008. <http://dx.doi.org/10.1007/s11367-016-1069-x>.
- 17 Schrijvers, D., Loubet, P., Sonnemann, G., 2016b. Developing a systematic framework for consistent  
18 allocation in LCA. *Int J Life Cycle Assess.* 21, 976-993. <http://dx.doi.org/10.1007/s11367-016-1063-3>.
- 19
- 20 Stimilli, A., Virgili, A., Canestrari, F., 2017. Warm recycling of flexible pavements: effectiveness of  
21 Warm Mix Asphalt additives on modified bitumen and mixture performance. *J Clean Prod.* 156,  
22 911-922. <http://dx.doi.org/10.1016/j.jclepro.2017.03.235>.
- 23 Tatari, O., Nazzal, M., Kucukvar, M., 2012. Comparative sustainability assessment of warm-mix  
24 asphalts: a thermodynamic based hybrid life cycle analysis. *Resour. Conserv. Recycl.* 58, 18-24.  
25 <http://dx.doi.org/10.1016/j.resconrec.2011.07.005>.
- 26 Thives, L., Ghisi, E., 2017. Asphalt mixtures emission and energy consumption: a review. *Renewable  
27 Sustainable Energy Rev.* 72, 473-484. <http://dx.doi.org/10.1016/j.rser.2017.01.087>.
- 28 Transportation Research Board (TRB), 2000. *Highway Capacity Manual 2000*. Transportation  
29 Research Board, Washington, DC.
- 30 Van Dam, T., Harvey, J., Muench, S., Smith, K., Snyder, M., Al-Qadi, I., Ozer, H., Meijer, J., Ram, P.,  
31 Roesler, J., Kendall, A., 2015. *Towards sustainable pavement systems- a reference document*.  
32 Report No. FHWA-HIF-15-002, Federal Highway Administration, Washington, DC.
- 33 Vidal, R., Moliner, E., Martínez, G., Rubio, M., 2013. Life cycle assessment of hot mix asphalt and  
34 zeolite-based warm mix asphalt with reclaimed asphalt pavement. *Resour. Conserv. Recycl.* 74,  
35 101-114. <http://dx.doi.org/10.1016/j.resconrec.2013.02.018>.
- 36 Washington State University, Pennsylvania State University–Altoona, Louisiana Transportation  
37 Research Center, 2017. *Long-term field performance of warm mix asphalt technologies*. NCHRP  
38 Research Report 843, Transportation Research Board, Washington, D.C.
- 39 West, R., Rodezno, C., Julian, G., Prowell, B., Frank, B., Osborn, L., Kriech, T., 2014. *Field  
40 Performance of Warm Mix Asphalt Technologies (National Cooperative Highway Research  
41 Program Report No. 779)*. Transportation Research Board, Washington, D.C.
- 42 Yang, X., You, Z., Hasan, M., Diab, A., Shao, H., Chen, S., Ge, D., 2017. Environmental and  
43 mechanical performance of crumb rubber modified warm mix asphalt using Evotherm. *J Clean  
44 Prod.* 159, 346-358. <http://dx.doi.org/10.1016/j.jclepro.2017.04.168>.
- 45 Zaumanis, M., 2014. Warm mix asphalt, in: Gopalakrishnan, K., Steyn, W., Harvey, J. (Eds.), *Climate  
46 Change, Energy, Sustainability and Pavements*, Green Energy and Technology, Springer-Verlag.  
47 [http://dx.doi.org/10.1007/978-3-662-44719-2\\_10](http://dx.doi.org/10.1007/978-3-662-44719-2_10).